

Adsorption Kinetics and Isotherms of Cu(II) and Fe(II) Ions from Aqueous Solutions by Fly Ash-Based Geopolymer

by Aprilina Purbasari

Submission date: 24-Jan-2023 08:35AM (UTC+0700)

Submission ID: 1998123601

File name: Chemistry__Chemical_Technology_artikel.pdf (250.6K)

Word count: 3961

Character count: 19996

ADSORPTION KINETICS AND ISOTHERMS OF Cu(II) AND Fe(II) IONS FROM AQUEOUS SOLUTIONS BY FLY ASH-BASED GEOPOLYMER

Aprilina Purbasari¹, Dessy Ariyanti¹, Siswo Sumardiono¹, Khansa Khairunnisa¹, Tyaga Sidharta¹

<https://doi.org/10.23939/chcht16.02.169>

Abstract. This paper describes the adsorption of Cu²⁺ and Fe²⁺ ions, common heavy metals found in industrial wastewater, by a fly ash-based geopolymer in batch adsorption experiments. Kinetics studies showed that the adsorption of each ion followed a pseudo-second order reaction. Moreover, adsorption isotherm of Cu²⁺ and Fe²⁺ ions followed the Langmuir model. Monolayer adsorption capacities were approximately 53.76 mg/g for Cu²⁺ ion and 52.63 mg/g for Fe²⁺ ion, respectively.¹

Keywords: adsorption, Cu(II) ion, Fe(II) ion, fly ash-based geopolymer, Langmuir isotherm, pseudo second order reaction.

1. Introduction

Geopolymers are mineral polymers with Si–O–Al bonds formed from aluminosilicate materials with alkaline activators at the temperature below 373 K. Aluminosilicate materials used as a geopolymer raw material can come from nature such as kaolin or metakaolin (calcined kaolin) and solid wastes such as fly ash and slag. Alkaline activators commonly used in geopolymer production are sodium hydroxide solution, potassium hydroxide solution, mixture of sodium hydroxide solution and sodium silicate solution, mixture of potassium hydroxide solution and potassium silicate solution. Geopolymers have been widely applied as a building material, coatings, adhesives, composites, and waste encapsulation.¹

Fly ash is a by-product from coal combustion at power plant. Fly ash which is solid waste can be utilized

as additives in cement industry, road construction, mine reclamation, etc. Fly ash containing silica and alumina can also be utilized as a geopolymer raw material.^{2–4} Fly ash-based geopolymer has been widely used as Portland cement substitute because it has a high mechanical strength, resistance to corrosive environment, and less CO₂ emissions.^{5,6}

Geopolymers with amorphous to semi-crystalline three dimensional structures have pores that potentially are to be used as an adsorbent, for example the heavy metal adsorbent. This is also supported by the presence of negative charge on aluminium in the geopolymer structure that will attract cation.^{7,8} Adsorption is one of the treatment methods of wastewater containing the heavy metal that is widely used due to relatively easy operation, high efficiency, low cost, and possibility of adsorbent regeneration.^{9–11} Copper and iron ions are common heavy metals found in industrial wastewater.¹² Long-term exposure of copper can cause headache, stomachache, and irritation of nose, mouth, eyes; while excess amounts of iron can cause rapid pulse rates, blood vessels congestion, and hypertension.¹³

In this research, the fly ash-based geopolymer was used as the adsorbent for Cu²⁺ and Fe²⁺ ions. Adsorption kinetics and isotherms that can describe the adsorption process were studied. In addition, the fly ash-based geopolymer was also characterized before and after the adsorption process. The results of this study were expected to contribute to the solid waste utilization for wastewater treatment.

2. Experimental

2.1. Geopolymer Preparation

Fly ash from power plants in East Java, Indonesia, was sieved with 200 mesh standard sieve before being used as the geopolymer raw material. The oxides content

¹ Department of Chemical Engineering, Faculty of Engineering, Diponegoro University
Jl. Prof. Soedarto, Kampus Tembalang, Semarang 50275, Indonesia
✉ aprilina.purbasari@che.undip.ac.id
© Purbasari, A.; Ariyanti, D.; Sumardiono, S.; Khairunnisa, K.; Sidharta, T., 2022

in the fly ash based on X-ray fluorescence (XRF) analysis is shown in Table 1. The silica and alumina contents in the fly ash are high enough so that fly ash can be used as the raw material for the geopolymer.

Fly ash was mixed with an alkaline activator for 10 min to form the geopolymer. The ratio of fly ash to the alkaline activator was 2.5:1. Alkaline activator consisted of 10N NaOH solution and Na-silicate solution with the ratio of 1:1. Na-silicate solution had $\text{SiO}_2/\text{Na}_2\text{O}$

mole ratio of 3.2 and solid mass fraction of 0.35. The mixture was placed in a 5×5×5 cm mold and cured for 24 h. After removing from the mold, the geopolymer was cured in an oven at 333 K for 6 h and then at room temperature for 7 days. The geopolymer was crushed and sieved with 50 mesh standard sieve to obtain geopolymer powder used as the heavy metal adsorbent. Geopolymer powder had Brunauer-Emmett-Teller (BET) surface area of 27.205 m^2/g .

Table 1. Oxides content in fly ash

Oxide	wt %	Oxide	wt %	Oxide	wt %	Oxide	wt %
SiO_2	42.382	MgO	4.721	ZnO	0.011	Others	0.875
Al_2O_3	22.62	K_2O	1.118	TiO_2	0.957		
CaO	14.796	CuO	0.008	P_2O_5	0.604		
Fe_2O_3	9.447	MnO	0.092	SO_3	2.369		

2.2. Adsorption Experiment

Solutions of Cu^{2+} and Fe^{2+} were each prepared by dissolving the analytical grade $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$ and $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ with distilled water. Batch adsorption experiments were carried out on 100 ml heavy metal solution at room temperature (301 K) with geopolymer dosage of 0.2 g, pH of 5, and stirring rate of 200 rpm. Kinetics studies were conducted with varying adsorption time (15–180 min) at the initial concentration of heavy metal solution of 100 ppm. Meanwhile, isotherm studies were conducted with a varying initial concentration of heavy metal solution (10–150 ppm) at adsorption time of 2 h. The concentrations of Cu^{2+} and Fe^{2+} solutions were each measured by atomic absorption spectroscopy (AAS) with a removal efficiency (%) as follows:

$$\text{Removal efficiency} = \frac{C_0 - C_e}{C_0} \cdot 100\% \quad (1)$$

where C_0 and C_e are the initial and equilibrium concentrations of heavy metal solution, respectively.

2.3. Characterization

Characterization of geopolymer before and after adsorption process comprised X-ray diffraction (XRD) analysis and Fourier transform infrared spectroscopy (FTIR) analysis. XRD analysis was conducted with a Shimadzu XRD-7000 instrument under following

conditions: 30 kV, 30 mA, $\text{CuK}\alpha$ radiation, and $2\theta = 5\text{--}90^\circ$. FTIR analysis was conducted with a Shimadzu IR Prestige-21 instrument with KBr pellet technique in the wavenumber range of 4000–400 cm^{-1} .

3. Results and Discussion

3.1. The Effect of Adsorption Time and Adsorption Kinetics

The effect of adsorption time on the removal efficiency of Cu^{2+} and Fe^{2+} ions is shown in Fig. 1. The increase in the adsorption time caused the increase in the removal efficiency until it did not change. This indicated that the adsorption process had reached equilibrium. The adsorption process of Cu^{2+} and Fe^{2+} ions by the fly ash-based geopolymer had reached equilibrium after 120 min.

Studies on the effect of adsorption time can provide information related to the mechanism of adsorption process that determined by a kinetic model. The expression for adsorption kinetics models are:¹⁴

- A pseudo-first order reaction:

$$\ln(q_e - q_t) = \ln q_e - k_1 t \quad (2)$$

- A pseudo-second order reaction:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e} \quad (3)$$

where k_1 and k_2 are the pseudo-first order and the pseudo-second order reaction constants, respectively; q_e

34

and q_t are the amounts of adsorbed metal ions or adsorption capacity at equilibrium and at time t , respectively.

Linear fittings of the pseudo-first order kinetics model, namely $\ln(q_e - q_t)$ vs. t , for adsorption of Cu^{2+} and Fe^{2+} ions by the fly ash-based geopolymer are shown in Fig. 2, while linear fittings of the pseudo-second order kinetics model, namely t/q_t vs. t , in Fig. 3. The obtained

adsorption kinetics parameters are listed in Table 2. Adsorption process followed the pseudo-second order kinetics model with a coefficient of correlation (R^2) of 0.992 and 0.997 for Cu^{2+} and Fe^{2+} , respectively. Thus the adsorption of Cu^{2+} and Fe^{2+} ions by the fly ash-based geopolymer was controlled by the chemical adsorption process.^{15,16} These result were similar to those obtained by other researches.^{14,17-19}

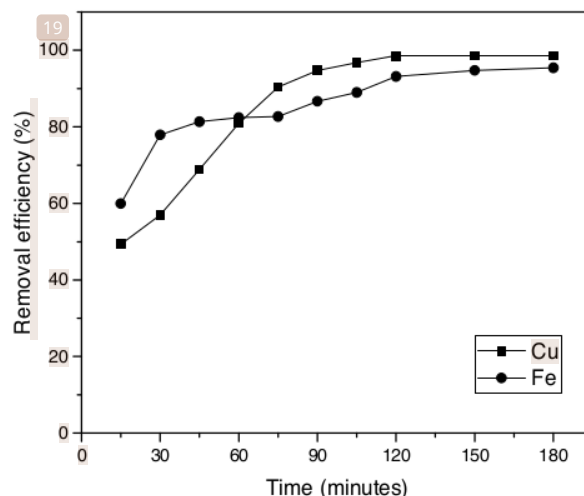


Fig. 1. Effect of adsorption time on Cu^{2+} and Fe^{2+} ions removal efficiency

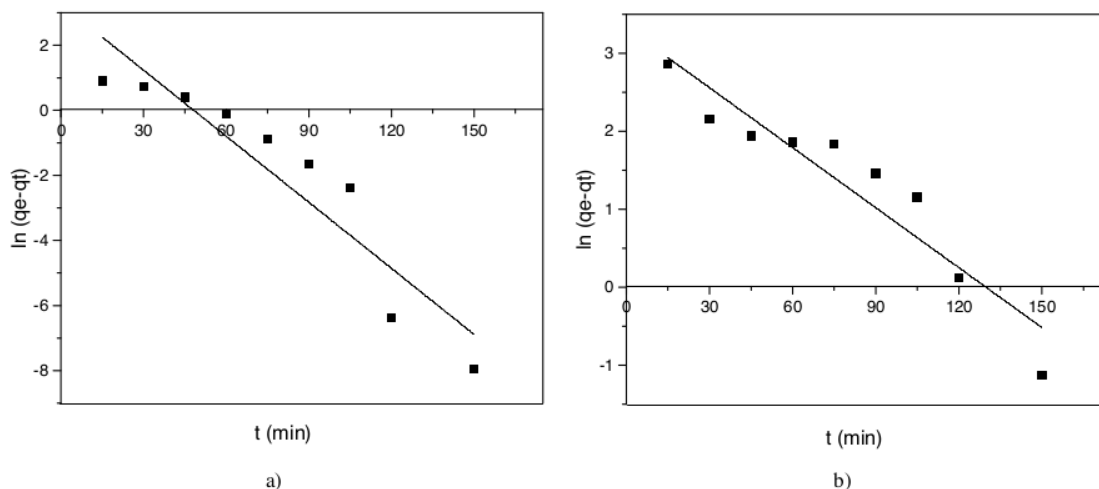


Fig. 2. Linear fittings of the pseudo-first order kinetics model for adsorption of Cu^{2+} (a) and Fe^{2+} (b) ions by the fly ash-based geopolymer

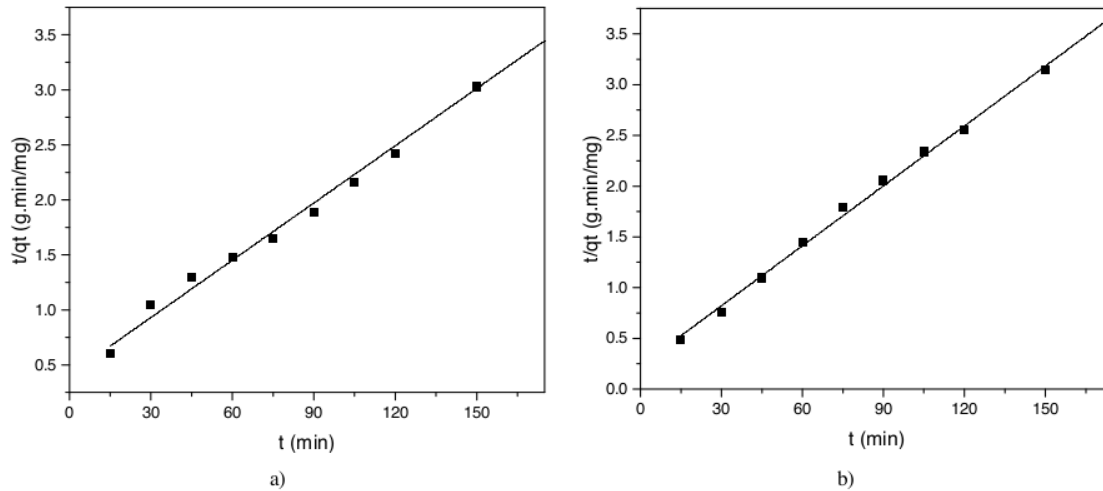


Fig. 3. Linear fitting of pseudo second order kinetics model for adsorption of Cu^{2+} (a) and Fe^{2+} (b) ions by the fly ash-based geopolymer

Table 2. Adsorption kinetics parameters for adsorption of Cu^{2+} and Fe^{2+} ions by the fly ash-based geopolymer

Metal ion	Pseudo-first order kinetics model			Pseudo-second order kinetics model		
	$q_e, \text{mg} \cdot \text{g}^{-1}$	k_1, min^{-1}	R^2	$q_e, \text{mg} \cdot \text{g}^{-1}$	$k_2, \text{g} \cdot \text{mg}^{-1} \cdot \text{min}^{-1}$	R^2
Cu^{2+}	26.102	0.067	0.872	52.804	0.000727	0.992
Fe^{2+}	27.910	0.025	0.889	51.020	0.001657	0.997

3.2. The Effect of Initial Concentration and Adsorption Isotherm

The effect of initial concentration on Cu^{2+} and Fe^{2+} ions removal efficiency is shown in Fig. 4. The increase of initial concentration would decrease the removal efficiency. At low concentration of adsorbate, the adsorbent had the sufficient surface to adsorb the adsorbate. However, if concentration of adsorbate was increased continuously then the surface of the adsorbent was no longer sufficient to adsorb the adsorbate.²⁰

The interaction between the adsorbent and the adsorbate can be studied from the adsorption isotherm equilibrium model. Adsorption isotherm equilibrium model can be determined with the varying initial concentration of adsorbate at constant adsorbent dosage. Common equilibrium models of adsorption isotherm are the Langmuir isotherm and the Freundlich isotherm.¹⁸

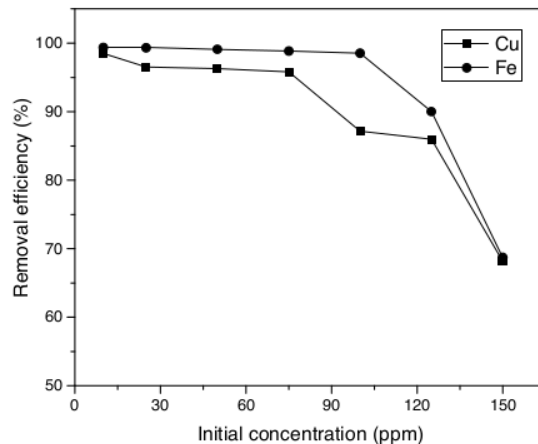


Fig. 4. Effect of initial concentration on Cu^{2+} and Fe^{2+} ions removal efficiency

Langmuir isotherm

In this model, the adsorbent is assumed to have a whole homogeneous surface and each adsorbent molecule

can only adsorb one adsorbate molecule so that there is only one layer of adsorbate on the surface of the adsorbent. The Langmuir isotherm equation is expressed as:

$$q_e = \frac{q_m K_L C_e}{1 + K_L C_e} \quad (4)$$

where C_e is the equilibrium concentration, q_m is the maximum adsorption capacity and K_L is the Langmuir constant.

Freundlich isotherm

The adsorbent is assumed to have a heterogeneous surface in this model so that each adsorbent molecule has different adsorption abilities. The equation for Freundlich isotherm is expressed as:

$$q_e = K_F C_e^{\frac{1}{n}} \quad (5)$$

where K_F is Freundlich constant which is related to the adsorption capacity, $1/n$ is related to the adsorption intensity.

Fig. 5 shows linear fittings of Langmuir isotherm (C_e/q_e vs. C_e) and Fig. 6 shows linear fittings of Freundlich isotherm ($\log q_e$ vs. $\log C_e$) for the adsorption process of Cu^{2+} and Fe^{2+} ions by the fly ash-based geopolymer with adsorption isotherm parameters listed in Table 3. Based on coefficient of correlation (R^2), the Langmuir isotherm model was more appropriate to explain the adsorption of Cu^{2+} and Fe^{2+} ions by the geopolymer. Therefore, the adsorption of Cu^{2+} and Fe^{2+} ions by the geopolymer was the monolayer adsorption. Similar results were also obtained by other researches.^{14, 17-19}

Characteristics of Langmuir isotherm can be expressed by a dimensionless separation factor (R_L) calculated with the following equation:

$$R_L = \frac{1}{1 + K_L C_0} \quad (6)$$

where K_L is Langmuir constant and C_0 is initial concentration.

The adsorption process can be categorized favorable when $0 < R_L < 1$; unfavorable when $R_L > 1$; linear when $R_L = 1$, and irreversible when $R_L = 0$.²¹ The adsorption of Cu^{2+} ion by geopolymer with initial concentration of 10–150 ppm had R_L values of 0.166–0.013 so it can be categorized as favorable adsorption. Likewise, the adsorption of Fe^{2+} ion by geopolymer with initial concentration of 10–150 ppm had R_L values of 0.021–0.001 and can also be categorized as favorable adsorption.

3.3. Characterizations

XRD pattern of geopolymer before and after the adsorption process of Cu^{2+} and Fe^{2+} ions are shown in Fig. 7. Broad diffraction hump in the region of $20\text{--}40^\circ$ (2θ) indicated the presence of amorphous phases. Meanwhile, the sharp peak at around 26° (2θ) came from quartz.⁴ The intensity of the peaks in the geopolymer after the adsorption process did not seem to differ much compared to those in the geopolymer before the adsorption process. This indicated that the adsorption process of Cu^{2+} and Fe^{2+} ions had occurred on the surface of geopolymer.^{22,23}

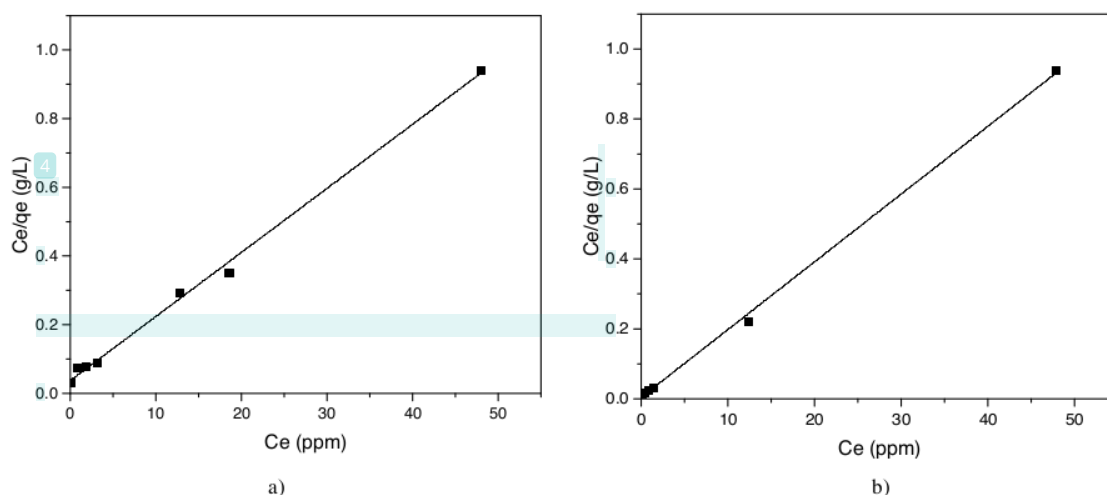


Fig. 5. Linear fitting of Langmuir isotherm for adsorption of Cu^{2+} (a) and Fe^{2+} (b) ions by the fly ash-based geopolymer

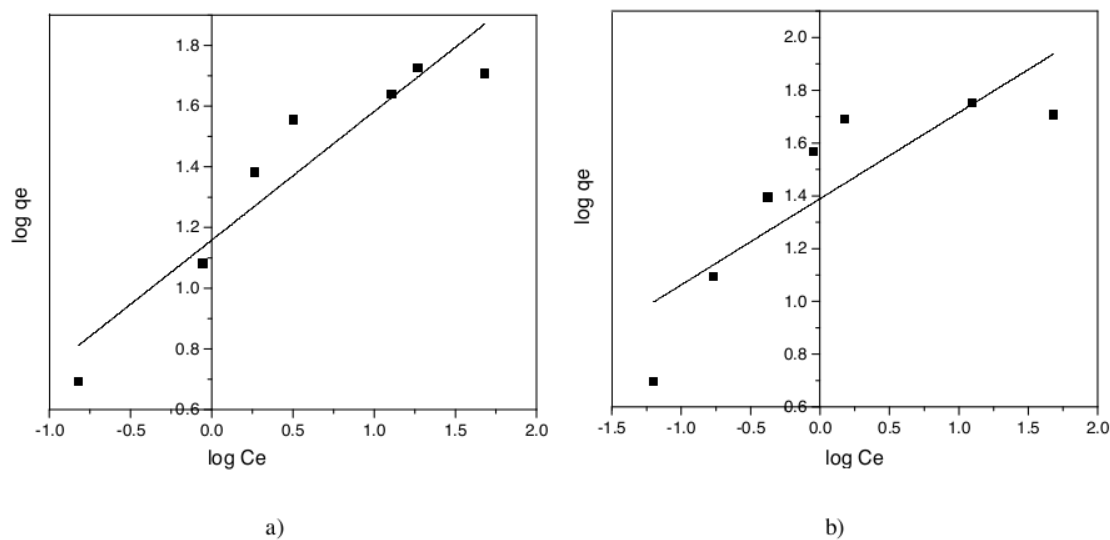


Fig. 6. Linear fitting of Freundlich isotherm for adsorption of Cu^{2+} (a) and Fe^{2+} (b) ions by the fly ash-based geopolymer

Table 3. Adsorption isotherm parameters for adsorption of Cu^{2+} and Fe^{2+} ions by the fly ash-based geopolymer

Metal ion	Langmuir model			Freundlich model		
	$q_m, \text{mg} \cdot \text{g}^{-1}$	$K_L, \text{L} \cdot \text{mg}^{-1}$	R^2	$1/n$	$K_F, \text{mg} \cdot \text{g}^{-1} (\text{L} \cdot \text{mg}^{-1})^{1/n}$	R^2
Cu^{2+}	53.763	0.503	0.996	0.423	14.388	0.897
Fe^{2+}	52.632	4.750	0.998	0.326	24.491	0.717

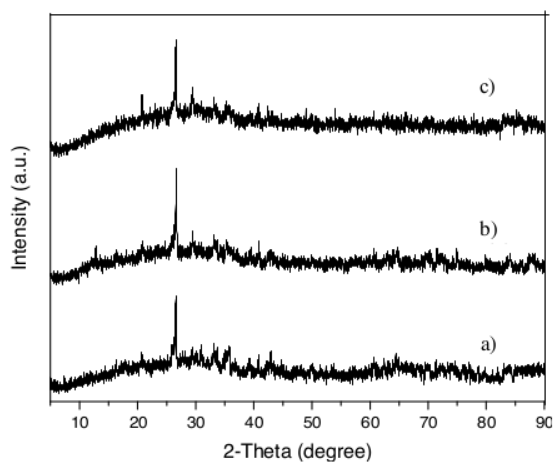


Fig. 7. XRD pattern of geopolymer before the adsorption process (a) and the geopolymer after the adsorption process of Cu^{2+} (b) and Fe^{2+} (c) ions

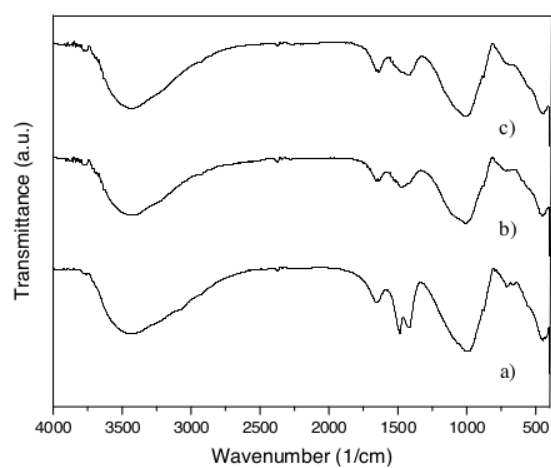


Fig. 8. FTIR spectra of geopolymer before the adsorption process (a) and the geopolymer after the adsorption process of Cu^{2+} (b) and Fe^{2+} (c) ions

Fig. 8 shows FTIR spectra of geopolymer before and after the adsorption process of Cu^{2+} and Fe^{2+} ions. Geopolymer before and after the adsorption process contained the same functional groups, namely Si–O–Si and O–Si–O (bending vibration) at the wavenumber of about 470 cm^{-1} , Si–O–Si (symmetrical stretching vibration) at about 795 cm^{-1} , Si(Al)–O (asymmetrical vibration) at about 1008 cm^{-1} , O–C–O (stretching vibration) at about 1410 cm^{-1} , HOH (bending vibration) at about 1650 cm^{-1} , –OH and HOH (stretching vibration) at about 3400 cm^{-1} .²⁴⁻²⁶ The presence of O–C–O group showed that the presence of carbonate that can be formed from the atmospheric CO_2 , while –OH and HOH groups showed the presence of adsorbed atmospheric water.²⁷

The peaks of functional group in the geopolymer after the adsorption process did not appear to change much compared to those in the geopolymer before the adsorption process. The apparent change in intensity came from O–C–O group in which the peak intensity in the geopolymer after adsorption process appeared to be smaller than that in the geopolymer before the adsorption process. This was due to the adsorption process that took place in the acidic solution (pH 5) that can dissolve the formed carbonate.²⁸

4. Conclusions

Fly ash-based geopolymer had been prepared and utilized as the adsorbent for Cu^{2+} and Fe^{2+} ions from the aqueous solutions. The kinetics studies showed that the adsorption of Cu^{2+} and Fe^{2+} ions followed the pseudo-second order reaction or controlled by the chemical adsorption process with the coefficient of correlation $R^2 > 0.99$. Furthermore, the adsorption isotherm of Cu^{2+} and Fe^{2+} ions followed Langmuir model or monolayer adsorption with each $R^2 > 0.99$ based on adsorption isotherm studies. Maximum adsorption capacity of fly ash-based geopolymer on Cu^{2+} ion was slightly higher than that on Fe^{2+} ion, namely 53.76 mg/g for Cu^{2+} ion and 52.63 mg/g for Fe^{2+} ion.

Acknowledgments

This research was financially supported by Directorate of Research and Community Service, Directorate General of Research and Development Strengthening,

Ministry of Research, Technology and Higher Education, Indonesia through Program of Higher Education Basic Research 2019.

References

- [1] Davidovits, J. Geopolymers: Ceramic-Like Inorganic Polymers. *J. Ceram. Sci. Technol.* **2017**, *8*, 335-350. <https://doi.org/10.4416/JCST2017-00038>
- [2] Kramar, S.; Ducman, V. Mechanical and Microstructural Characterization of Geopolymer Synthesized from Low Calcium Fly Ash. *Chem. Ind. Chem. Eng. Q.* **2015**, *21*, 13-22. <https://doi.org/10.2298/CICEQ130725042K>
- [3] Bhatnagar, A.; Minocha, A.K. Conventional and Non-Conventional Adsorbents for Removal of Pollutants From Water – A Review. *Indian J. Chem. Technol.* **2006**, *13*, 203-217. <http://nopr.niscair.res.in/handle/123456789/7020>
- [4] Alehyen, S.; Achouri, M.; Taibi, M. Characterization, Microstructure and Properties of Fly Ash-Based Geopolymer. *J. Mater. Environ. Sci.*, 2017, *8*, 1783-1796.
- [5] Zhuang, X.Y.; Chen, L.; Komarneni, S.; Zhou, C.H.; Tong, D.S.; Yang, H.M.; Yu, W.H.; Wang, H. Fly Ash-Based Geopolymer: Clean Production, Properties and Applications. *J. Clean. Prod.* **2016**, *125*, 253-267. <https://doi.org/10.1016/j.jclepro.2016.03.019>
- [6] Singh, N.B. Fly Ash-Based Geopolymer Binder: A Future Construction Material. *Minerals* **2018**, *8*, 299-320. <https://doi.org/10.3390/min8070299>
- [7] Siyal, A.A.; Shamsuddin, M.R.; Khan, M.I.; Rabat, N.E.; Zulfiqar, M.; Man, Z.; Siame, J.; Azizli, K.A. A Review on Geopolymers as Emerging Materials for the Adsorption of Heavy Metals and Dyes. *J. Environ. Manage.* **2018**, *224*, 327-339. <https://doi.org/10.1016/j.jenvman.2018.07.046>
- [8] Rasaki, S.A.; Bingxue, Z.; Guarecuco, R.; Thomas, T.; Minghui, Y. Geopolymer for Use in Heavy Metals Adsorption, and Advanced Oxidative Processes: A Critical Review. *J. Clean. Prod.* **2019**, *213*, 42-58. <https://doi.org/10.1016/j.jclepro.2018.12.145>
- [9] Iakovleva, E.; Sillanpää, M. The Use of Low-Cost Adsorbents for Wastewater Purification in Mining Industries. *Environ. Sci. Pollut. Res.* **2013**, *20*, 7878-7899. <https://doi.org/10.1007/s11356-013-1546-8>
- [10] Lim, A.P.; Aris, A.Z. A Review on Economically Adsorbents on Heavy Metals Removal in Water and Wastewater. *Rev. Environ. Sci. Biotechnol.* **2014**, *13*, 163-181. <https://doi.org/10.1007/s11157-013-9330-2>
- [11] Sabadash, V.; Mylanyk, O.; Matsuska, O.; Gumniatsky, J. Kinetic Regularities of Copper Ions Adsorption by Natural Zeolite. *Chem. Chem. Technol.* **2017**, *11*, 459-462. <https://doi.org/10.23939/chcht11.04.459>
- [12] Al-Saydeh, S.A.; El-Naas, M.H.; Zaidi, S.J. Copper Removal from Industrial Wastewater: A Comprehensive Review. *J. Ind. Eng. Chem.* **2017**, *56*, 35-44. <https://doi.org/10.1016/j.jiec.2017.07.026>
- [13] Ahmaruzzaman, M. Industrial Wastes as Low-Cost Potential Adsorbents for the Treatment of Wastewater Laden with Heavy

- Metals. *Adv. Colloid Interface Sci.* **2011**, 166, 36-59. <https://doi.org/10.1016/j.cis.2011.04.005>
- [14] Ge, Y.; Cui, X.; Kong, Y.; Li, Z.; He, Y.; Zhou, Q. Porous Geopolymeric Spheres for Removal of Cu(II) from Aqueous Solution: Synthesis and Evaluation. *J. Hazard. Mater.* **2015**, 283, 244-251. <https://doi.org/10.1016/j.jhazmat.2014.09.038>
- [15] Abas, S.N.A.; Ismail, M.H.S.; Kamal, M.L.; Izhar, S. Adsorption Process of Heavy Metals by Low-Cost Adsorbent: A Review. *World Appl. Sci. J.* **2013**, 28, 1518-1530.
- [16] Nguyen, K.M.; Nguyen, B.Q.; Nguyen H.T.; Nguyen H.T.H. Adsorption of Arsenic and Heavy Metals from Solutions by Unmodified Iron-Ore Sludge. *Appl. Sci.* **2019**, 9, 619-633. <https://doi.org/10.3390/app9040619>
- [17] Al-Zboon, K.; Al-Harashsheh, M.S.; Hani, F.B. Fly Ash-Based Geopolymer for Pb Removal from Aqueous Solution. *J. Hazard. Mater.* **2011**, 188, 414-421. <https://doi.org/10.1016/j.jhazmat.2011.01.133>
- [18] Al-Harashsheh, M.S.; Al-Zboon, K.; Al-Makhadmeh, L.; Hararah, M.; Mahasneh, M. Fly Ash Based Geopolymer for Heavy Metal Removal: A Case Study on Copper Removal. *J. Environ. Chem. Eng.* **2015**, 3, 1669-1677. <https://doi.org/10.1016/j.jece.2015.06.005>
- [19] Qiu, J.; Zhao, Y.; Xing, J.; Sun, X. Fly Ash-Based Geopolymer as a Potential Adsorbent for Cr(VI) Removal. *Desalin. Water Treat.* **2017**, 70, 201-209. <https://doi.org/10.5004/dwt.2017.20493>
- [20] Duan, P.; Yan, C.; Zhou, W.; Ren, D. Development of Fly Ash and Iron Ore Tailing Based Porous Geopolymer for Removal of Cu(II) from Wastewater. *Ceram. Int.* **2016**, 42, 13507-13518. <https://doi.org/10.1016/j.ceramint.2016.05.143>
- [21] Ayawei, N.; Ebelegi, A.N.; Wankasi, D. Modelling and Interpretation of Adsorption Isotherms. *J. Chem.* **2017**, 2017, 3039817. <https://doi.org/10.1155/2017/3039817>
- [22] Karthikeyan, G.; Siva Ilango, S. Equilibrium Sorption Studies of Fe, Cu and Co Ions in Aqueous Medium Using Activated Carbon Prepared from Recinius Communis Linn. *J. Appl. Sci. Environ. Manage.* **2008**, 12, 81-87. <https://doi.org/10.4314/jasem.v12i2.55537>
- [23] Sarkar, C.; Basu, J.K.; Samanta, A.N. Synthesis of Mesoporous Geopolymeric Powder from LD Slag as Superior Adsorbent for Zinc (II) Removal. *Adv. Powder Technol.* **2018**, 29, 1142-1152. <https://doi.org/10.1016/j.apt.2018.02.005>
- [24] Davidovits, J. *Geopolymer: Chemistry and Applications*; Institut Géopolymère: Saint-Quentin, 2008.
- [25] Lee, W.K.W.; van Deventer, J.S.J. Structural Reorganisation of Class F Fly Ash in Alkaline Silicate Solutions. *Colloid Surface A* **2002**, 211, 49-66. [https://doi.org/10.1016/S0927-7757\(02\)00237-6](https://doi.org/10.1016/S0927-7757(02)00237-6)
- [26] Lee, W.K.W.; van Deventer, J.S.J. The Effects of Inorganic Salt Contamination on the Strength and Durability of Geopolymers. *Colloid Surface A* **2002**, 211, 115-126. [https://doi.org/10.1016/S0927-7757\(02\)00239-X](https://doi.org/10.1016/S0927-7757(02)00239-X)
- [27] Nath, S.K.; Maitra, S.; Mukherjee, S.; Kumar S. Microstructural and Morphological Evolution of Fly Ash Based Geopolymers. *Constr. Build. Mater.* **2016**, 111, 758-765. <https://doi.org/10.1016/j.conbuildmat.2016.02.106>
- [28] Bouguermouh, K.; Bouzidi, N.; Mahtout, L.; Pérez-Villarejo, L.; Martínez-Cartas, M.L. Effect of Acid Attack on Microstructure and Composition of Metakaolin-Based Geopolymers: The Role of Alkaline Activator. *J. Non-Cryst. Solids* **2017**, 463, 128-137. <https://doi.org/10.1016/j.jnoncrysol.2017.03.011>

Received: January 20, 2020 / Revised: March 03, 2020 /

Accepted: May 12, 2020

КІНЕТИКА АДСОРБЦІЇ ТА ІЗОТЕРМИ ЙОНІВ Cu(II) І Fe(II) З ВОДНИХ РОЗЧИНІВ З ВИКОРИСТАННЯМ ГЕОПОЛІМЕРУ НА ОСНОВІ ЗОЛИ ВІНОСУ

Анотація. Експериментально досліджено адсорбцію йонів Cu^{2+} та Fe^{2+} , звичайних важких металів, що знаходяться в промислових стічних водах, геополімером на основі золи виносу. Встановлено, що адсорбція кожного йона відбувається за реакцією псевдодругого порядку. Доведено, що ізотерна адсорбції йонів Cu^{2+} та Fe^{2+} відповідає моделі Ленгмюра. Визначено, що моношарова адсорбційна здатність становила приблизно 53,76 мг/г та 52,63 мг/г для йонів Cu^{2+} та Fe^{2+} , відповідно.

Ключові слова: адсорбція, йон Cu(II), йон Fe(II), геополімер на основі золи виносу, ізотерна Ленгмюра, реакція псевдодругого порядку.

Adsorption Kinetics and Isotherms of Cu(II) and Fe(II) Ions from Aqueous Solutions by Fly Ash-Based Geopolymer

ORIGINALITY REPORT

13%

SIMILARITY INDEX

8%

INTERNET SOURCES

9%

PUBLICATIONS

4%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|---|----------------|
| <div style="background-color: red; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">1</div> | <p>Aditya Shankar Ghosh, Tapash Kumar Roy.
"Chapter 18 Evaluating the Utility of Pond Ash as an Alternative Foundation Material Partially Replacing Sand for Foundation Layers", Springer Science and Business Media LLC, 2022</p> <p>Publication</p> | <p><1 %</p> |
| <hr/> | | |
| <div style="background-color: magenta; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">2</div> | <p>Anvit Gadkar, Kolluru V.L. Subramaniam.
"Porosity and pore structure control in cellular geopolymer using rheology and surface tension modifiers", Construction and Building Materials, 2022</p> <p>Publication</p> | <p><1 %</p> |
| <hr/> | | |
| <div style="background-color: purple; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">3</div> | <p>Francis N. Okoye, Satya Prakash, Nakshatra B. Singh. "Durability of fly ash based geopolymer concrete in the presence of silica fume", Journal of Cleaner Production, 2017</p> <p>Publication</p> | <p><1 %</p> |
| <hr/> | | |
| <div style="background-color: teal; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">4</div> | <p>Submitted to University of Hull</p> <p>Student Paper</p> | <p><1 %</p> |
-

5

Duan, Ping, Chunjie Yan, Wei Zhou, and Daming Ren. "Development of fly ash and iron ore tailing based porous geopolymer for removal of Cu(II) from wastewater", *Ceramics International*, 2016.

Publication

<1 %

6

Sujitra Onutai, Takaomi Kobayashi, Parjaree Thavorniti, Sirithan Jiemsirilars. "The Adsorption of Cadmium Ions on Fly Ash Based Geopolymer Particles", *Key Engineering Materials*, 2018

Publication

<1 %

7

Submitted to Universiti Teknologi Petronas

Student Paper

<1 %

8

Submitted to University of Witwatersrand

Student Paper

<1 %

9

ufdcimages.uflib.ufl.edu

Internet Source

<1 %

10

Hengels Castillo, Humberto Collado, Thomas Droguett, Sebastián Sánchez, Mario Vesely, Pamela Garrido, Sergio Palma. "Factors Affecting the Compressive Strength of Geopolymers: A Review", *Minerals*, 2021

Publication

<1 %

11

Yetilmezsoy, K.. "Artificial neural network (ANN) approach for modeling of Pb(II) adsorption from aqueous solution by Antep

<1 %

pistachio (Pistacia Vera L.) shells", Journal of Hazardous Materials, 20080530

Publication

12

www.journalrepository.org

Internet Source

<1 %

13

Franz, L.. "Different styles of metasomatic veining in ultramafic xenoliths from the TUBAF Seamount (Bismarck Microplate, Papua New Guinea)", LITHOS, 201001

Publication

<1 %

14

Submitted to University of Teesside

Student Paper

<1 %

15

doc-pak.undip.ac.id

Internet Source

<1 %

16

open.library.ubc.ca

Internet Source

<1 %

17

www.ijettjournal.org

Internet Source

<1 %

18

www.intechopen.com

Internet Source

<1 %

19

www.seas.ucla.edu

Internet Source

<1 %

20

A Khaeruni, T Wijayanto, M H Musa, M Rahayu, A Rahman, V N Satrah. "Effectiveness of the composition of bokashi organic materials on the ability of biofresh biological

<1 %

agents in inducing resistance of three maize varieties to sheath blight disease (Rhizoctonia solani)", IOP Conference Series: Earth and Environmental Science, 2020

Publication

21

C. Namasivayam, D. Sangeetha. " Removal of chromium(VI) by ZnCl activated coir pith carbon ", Toxicological & Environmental Chemistry, 2006

Publication

<1 %

22

Meryem Kerrou, Najia Bouslamti, Abdelaziz Raada, Abdellah Elanssari, Driss Mrani. "A comparative study of the kinetics and isotherm of adsorption of a cationic dye by different natural wastes", E3S Web of Conferences, 2021

Publication

<1 %

23

ena.lp.edu.ua

Internet Source

<1 %

24

real-phd.mtak.hu

Internet Source

<1 %

25

res.mdpi.com

Internet Source

<1 %

26

smallwatersystems.ucdavis.edu

Internet Source

<1 %

27

www.ije.ir

Internet Source

<1 %

<div style="background-color: #008080; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">28</div>	<p>Ana Cláudia da Costa Rocha, Gidiane Scaratti, Camilla Daniela Moura-Nickel, Thiago Lopes da Silva et al. "Economical and Technological Aspects of Copper Removal from Water Using a Geopolymer and Natural Zeolite", Water, Air, & Soil Pollution, 2020</p> <p>Publication</p>	<p><1 %</p>
---	---	----------------

<div style="background-color: #008000; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">29</div>	<p>Bo Ren, Yunliang Zhao, Haoyu Bai, Shichang Kang, Tingting Zhang, Shaoxian Song. "Eco-friendly geopolymer prepared from solid wastes: A critical review", Chemosphere, 2020</p> <p>Publication</p>	<p><1 %</p>
---	--	----------------

<div style="background-color: #8B4513; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">30</div>	<p>Krassimir Garbev. "Structural Features of C?S? H(I) and Its Carbonation in Air?A Raman Spectroscopic Study. Part I: Fresh Phases", Journal of the American Ceramic Society, 3/2007</p> <p>Publication</p>	<p><1 %</p>
---	--	----------------

<div style="background-color: #8B4513; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">31</div>	<p>Submitted to Midlands State University</p> <p>Student Paper</p>	<p><1 %</p>
---	--	----------------

<div style="background-color: #000080; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">32</div>	<p>jih.uobaghdad.edu.iq</p> <p>Internet Source</p>	<p><1 %</p>
---	--	----------------

<div style="background-color: #800080; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">33</div>	<p>pdfs.semanticscholar.org</p> <p>Internet Source</p>	<p><1 %</p>
---	--	----------------

<div style="background-color: #006400; color: white; display: inline-block; width: 40px; height: 40px; text-align: center; line-height: 40px;">34</div>	<p>www.internationaljournalssrg.org</p> <p>Internet Source</p>	<p><1 %</p>
---	--	----------------

35

Irene García-Díaz, Felix López, Francisco Alguacil. "Carbon Nanofibers: A New Adsorbent for Copper Removal from Wastewater", Metals, 2018

Publication

<1 %

36

materconstrucc.revistas.csic.es

Internet Source

<1 %

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

Adsorption Kinetics and Isotherms of Cu(II) and Fe(II) Ions from Aqueous Solutions by Fly Ash-Based Geopolymer

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7

PAGE 8