

Structural Analysis of Nanoceria Powder Precipitated in Different pH

by lis Nurhasanah

Submission date: 05-May-2023 02:24PM (UTC+0700)

Submission ID: 2084885399

File name: al_Analysis_of_Nanoceria_Powder_Precipitated_in_Different_pH.pdf (997.02K)

Word count: 1976

Character count: 11094

Structural Analysis of Nanoceria Powder Precipitated in Different pH

Iis Nurhasanah, Nurul Wahyu Puspaningrum, Ida Nursanti

Laboratory of Material Physics, Department of Physics
Faculty of Science and Mathematic, Diponegoro University
iisphysics@gmail.com

Received 27-02-2013, Revised 02-04-2013, Accepted 10-04-2013, Published 13-10-2013

ABSTRACT

Nanoceria has been proposed as inorganic material for sunscreen product because of its excellent UV absorption ability. Fine particle nanoceria and non-agglomeration determines comfort and covering capability on human skin. Particle size and agglomeration could be controlled by parameters and medium synthesis. In the present work, nanoceria powders were synthesized using precipitation method in different pH of 7 and 10. Precipitation was carried out in water/isopropanol mixed solvent. Cerium nitrate and ammonium hydroxide was used as source of cerium and precipitation agent, respectively. Crystal structure of nanoceria was examined using x-ray diffraction (XRD). Scanning electron microscope (SEM) was used to observe morphology of nanoceria. Diffraction pattern analysis shows that the precipitates were single phase of nanoceria with cubic fluorite structure and lattice constants of 0.5429 nm and 0.5419 nm. Crystallite size and lattice strain were obtained from Williamson-Hall method. Precipitation in pH of 7 resulted in smaller crystallite size which correlated to the larger lattice strain and lattice constant. SEM image shows spherical morphology with less agglomeration occurring for nanoceria precipitated in pH 10.

Keyword : nanoceria, precipitation method, XRD, SEM, agglomeration

ABSTRAK

Kemampuan absorpsivitas UV yang baik serbuk nanoceria menjadikannya sebagai material inorganik tabir surya. Serbuk nanoceria yang halus dan tidak bersifat aglomerasi menentukan kenyamanan penggunaannya. Ukuran nanoceria dan sifat aglomerasi dapat dikontrol oleh parameter dan medium sintesis. Serbuk nanoceria pada penelitian ini disintesis menggunakan metode presipitasi pada pH 7 dan 10 dalam campuran pelarut aquades/isopropanol. Cerium nitrate dan amonium hidroksida berturut-turut digunakan sebagai sumber cerium dan presipitan. Struktur kristal nanoceria diuji menggunakan difraksi sinar-x. Scanning electron microscope (SEM) digunakan untuk mengamati morfologi nanoceria. Analisis pola difraksi menunjukkan bahwa hasil presipitasi merupakan fase tunggal nanoceria berstruktur kubik fluorite dengan konstanta kisi 0,5419 nm dan 0,5429 nm. Kondisi presipitasi pada pH 7 menghasilkan ukuran kristalit yang lebih kecil. Ukuran kristalit yang kecil berkorelasi dengan regangan kisi dan konstanta kisi yang lebih besar. Citra SEM menggambarkan morfologi nanoceria berbentuk sferis dan aglomerasi lemah tampak pada nanoceria hasil presipitasi pada pH 10.

Kata kunci : nanoceria, metode presipitasi, XRD, SEM, aglomerasi

INTRODUCTION

Ceria has been used in many applications, such as: fuel cell^[1], gas sensor and pollutant reduction^[2-3], and anticorrosive coating^[4]. Recently, extensive investigation has been performed on potential ceria as nanobiomaterials^[5]. Because of excellent uv absorption ability, low photocatalytic, non-toxic and low refractive index is relatively transparent to

visible light, ceria is proposed as inorganic sunscreen material [6]. Three of the most important keys for sunscreen material are effective broad spectrum uv absorption, comfort and safety when applied on human skin. For those reasons, fine particle and non-agglomeration ceria is required.

Several methods have been used to synthesize nanoceria with controlled of properties. Precipitation method is the most attracted attention due to its advantages, such as: simple process, easy to scale-up, uniform particle size and low cost. In addition, diameter and distribution of particle size and morphology can be easily controlled by pH of synthesis. However, it is not easy to produce fine nanoceria using precipitation because of high degree agglomeration. Homogeneous precipitation with surfactant and precipitation in aqueous/alcohol mixed solvent are two approach which proposed to solve disadvantages of these method [7-9]. Usually, conventional precipitation method used water as a solvent. The addition of low dielectric solvent to the aqueous solution would result in reducing particle size and size distribution of resulting particles. Chen et al. employed six alcohols as the dielectric regulators of water/alcohol mixed solvents [9]. In other report, Sudjana used acetone as low dielectric medium and mixed with aqueous medium to prepare nanoceria by surfactant mediated precipitation method [10]. In the present work, nanoceria is synthesized using precipitation process in water/isopropanol mixed solvent with volume percentage of isopropanol was kept at 60% as previous reported [11]. Precipitation condition was adjusted in different pH. Structure and morphology of precipitates were studied.

EXPERIMENT

A solution of 0,08 M cerium nitrate hexahydrate (strem, 99,9%) was prepared in water/isopropanol (merck, 99,9 %) mixed solvent system. Nanoceria powder were obtained through precipitation process by dropwise 3 M ammonium hydroxide (merck) into cerium solution and stirred simultaneously under controlled pH of 7 and 10. The precipitates were washed with water and isopropanol. Finally, precipitates were dried at 60°C and then calcined at 300°C for 2 hours resulting in light yellowish powder. The structural characterization was performed by X-ray diffraction (Phillips PW 1710) using CuK α radiation. The morphology of powder was examined using a scanning electron microscope (JEOL, JSM 6360).

RESULTS AND DISCUSSION

The powder XRD patterns of nanoceria precipitated in different pH of 7 and 10 are shown in Figure 1. All the samples showed diffraction peaks of (111), (200), (220), (311), (222), (400), (331), (420) and (422) correspond to fluorite structure of ceria (JCPDS card no.43-0394). No secondary phase peak is found in the XRD pattern, which suggests that all samples are pure ceria. The diffraction peaks become narrower and sharper with increasing of precipitation pH, indicating the improvement of crystallinity.

Lattice constant for FCC structure was calculated by following equation:

$$= \frac{\lambda \sqrt{h^2 + k^2 + l^2}}{2 \sin \theta} \quad (1)$$

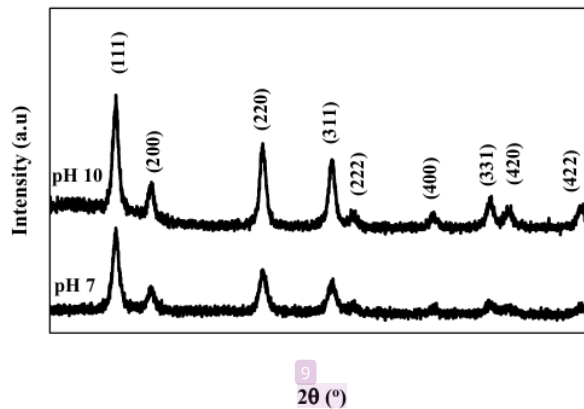


Figure 1. X-ray diffraction patterns of nanoceria precipitated in (a) pH 7, (b) pH 10

where, a is lattice constant of cubic crystal lattice, h , k and l Miller indices of the peak diffraction, λ denotes X-ray wavelength and θ the diffraction angle. From the XRD pattern, the full width at half maximum (FWHM) of all peak diffractions for nanoceria were also determined. The crystallite size and lattice strain were calculated according to Williamson-Hall equation as follow:

$$\frac{\cos}{\lambda} = - + 2 \frac{2 \sin}{\lambda}$$

OR

$$\Delta = \frac{0.89}{K} + 2 \quad (2)$$

In equation (2) Scherrer constant k is 0,89 for spherical particle, β denotes FWHM of peak diffraction and ε the lattice strain^[12]. Plots of Williamson-Hall equation are shown in Figure 2.

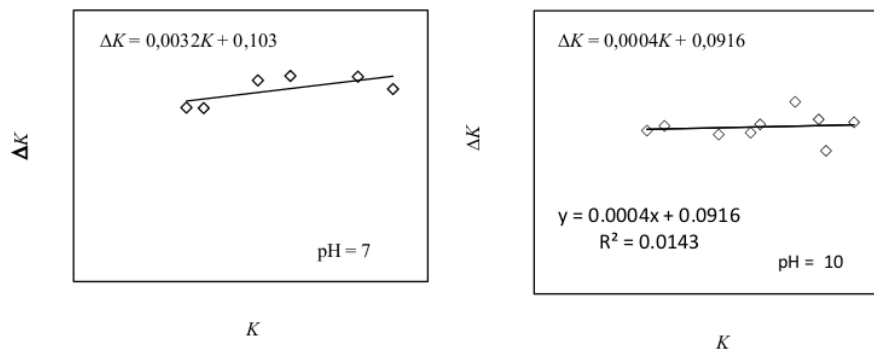


Figure 2. Williamson-Hall plots of nanoceria precipitated in (a) pH 7 and (b) pH 10

Table 1 summarizes crystallite size, lattice strain and lattice constant of nanoceria precipitated in pH 7 and pH 10 according to equation (1) and (2). Based on JCPDS card no. 43-0394, lattice constant of cubic phase ceria is 0.5411 nm. From the Table 1, it can

be seen that lattice constants are 0.5429 nm and 0.5419 nm for nanoceria precipitated in pH 7 and pH 10 respectively. The lattice constants are higher than that record on JCPDS card, indicate occurring lattice expansion. Its well known, generally nanoparticle of oxide exhibits lattice expansion with reduction in particle size. Therefore, the larger lattice constant of nanoceria precipitated in pH 7 is expected due to smaller crystallite size. As can be seen in Tabel 1, the crystallite sizes are 8.73 nm and 9.72 nm, respectively for pH 7 and pH 10. The precipitation condition in pH 7 resulting in smaller crystallite size which agreed to broader peak diffraction. The dependence of lattice constant to the crystallite size was also observed by Goharshadi et al. for nanoceria prepared by microwave method. An increase in lattice constant was correlated to a decrease in crystallite size^[13].

Table 1. Crystallite size, lattice strain and lattice constant of nanoceria precipitated in pH 7 and pH 10

pH	<i>D</i> (nm)	ϵ ($\times 10^{-3}$)	<i>a</i> (nm)
7	8,73	1.50	0.5429
10	9.72	0.20	0.5419

Figure 3 exhibits the spherical morphology of particle with diameter of about 10 nm - 30 nm which larger than that calculated crystallite size from XRD analysis. It is indicated that particle consists of one - three crystallite aggregates. Its also observed that particle size of nanoceria precipitated in pH 10 smaller than nanoceria precipitated in pH 7 suggesting that precipitation condition in pH 10 resulted in nanoceria with less agglomeration. These phenomenon can be explained as follow. Agglomeration is driven by surface energy. Smaller crystallite size is corelated to higher surface area and consequently the increase of that surface energy. Therefore, smaller crystallite size trends for hard agglomeration.

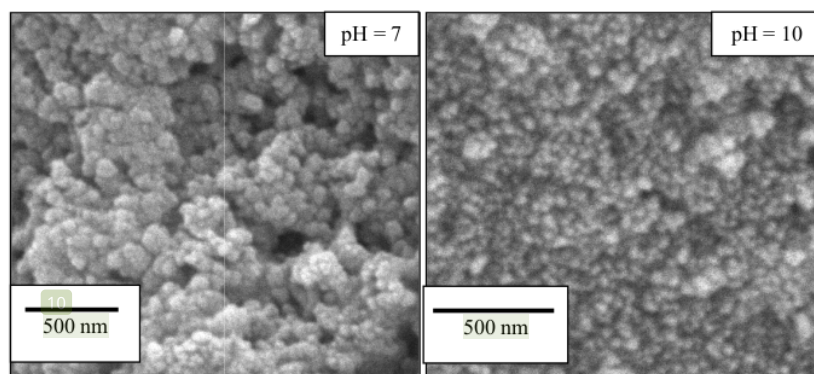


Figure 3. SEM images of nanoceria precipitated in (a) pH 7, (b) pH 10

CONCLUSION

Nanoceria powders can be prepared through precipitation process in pH of 7 and 10. The structure and morphology of nanoceria have been investigated by XRD and SEM. The prepared nanoceria had highly crystalline structure of cubic fluorite. pH of precipitation influences on crystallinity, crystallite size and agglomeration degree of nanoceria. Precipitation in pH 10 leads to bigger crystallite size and lattice constant closer to the reference. It also results in nanoceria with higher crystallinity and less agglomeration.

REFERENCES

- 1 Guo, D. J. and Jing, Z.H. 2010. A novel co-precipitation method for preparation of Pt-CeO₂ composites on multi-walled carbon nanotubes for direct methanol fuel cells, *J. Power Sources*, 195, 3802–3805.
- 2 Khan, S. B., Faisal, M., Rahman, M.M and Jamal, A. 2011. Exploration of CeO₂ nanoparticles as a chemi-sensor and photo-catalyst for environmental applications, *Sci. Total Environment*, 409, 2987-2992.
- 3 Liao, L., Mai, H. X., Yuan, Q., Lu, H. B., Li, J. C., Liu, C., Yan, C. H., Shen, Z. X and Yu, T. 2008. Single CeO₂ Nanowire Gas Sensor Supported with Pt Nanocrystals: Gas Sensitivity, Surface Bond States, and Chemical Mechanism, *J. Phys. Chem. C*, **112**, 9061-9065
- 4 Schem, M., Schmidt, T., Gerwann, J., Wittmar, M., Veith, M., Thompson G. E., Molchan, I. S., Hashimoto, T., Scheldon, P., Phani A. R., Santucci, S and Zheludkevich, M. L. 2009. CeO₂-filled sol-gel coating for corrosion protection of AA2024-T3 aluminium alloy. *Corrosion Sci.* 51, 2304-2315.
- 5 Karakoti, A.S., Monteiro-Riviere, N.A., Aggarwal, R., Davis, J.P., Narayan, R.J., Self, W.T., McGinnis, J and Seal, S. 2008. Nanoceria as Antioxidant: Synthesis and Bio-medical Applications. *Biomedical Materials Sci.*, 33-37.
- 6 Zholobak, N.M., Ivanov, V.K., Shcherbakov, A.B., Shaporev, A.S., Polezhaeva O.S., Ye, A., Baranchikov., Spivak, N.Ya., Tretyakov, Yu.D. 2011. UV-shielding property, photocatalytic activity and photocytotoxicity of ceriacolloid solutions, *J. Photochem. Photobio. B: Biology*. 102, 32–38.
- 7 Cho, M. Y., Roh, K. C., Park, S. M., Choi, H. J. and Lee, J. W. 2010. Control of particle size and shape of precursors for ceria using ammonium carbonate as a precipitant. *Mater. Lett*, 64, 323-326.
- 8 Zhai, Y., Zhang, S. and Pang, H. 2007. Preparation, characterization and photocatalytic activity of CeO₂ nanocrystalline using ammonium bicarbonat as precipitant. *Mater. Lett*, 61, 1863-1966.
- 9 Chen, H.I. and Chan, H. Y. 2004. Homogeneous precipitation of cerium dioxide nanoparticle in alcohols/water mixed-solvents, *Colloids and Surface A: Physicochem. Eng. Aspects*, 242, 61-69.
- 10 Sujana, M.G., Chattopadyay, K.K. and Anand, S. 2008. Characterization and optical properties of nano-ceria synthesized by surfactant-mediated precipitation technique in mixed solvent system, *App. Surf. Sci.*, 254, 7405 – 7409.
- 11 Nurhasanah, I., Nursanti, A.A.S., Nurdianik, H., Sutanto, Z., Muhlisin. 2011. Analisis difraksi sinar-x Nanokristalin CeO₂ yang disintesis dalam campuran pelarut air/alcohol. *Prosiding Seminar Nasional Inovasi dan Pembelajaran Sains*
- 12 Suryanarayana, C. and Norton, M. G. 1998. *X-Ray Diffraction : A Practical Approach*. Plenum Press : New York and London.
- 13 Goharshadi, E.K., Samiee, S. and Nancarrow, P. 2011. Fabrication of cerium oxide nanoparticles: Characterization and optical properties. *J. Coll. Interf. Sci*, 356, 473-480.

Structural Analysis of Nanoceria Powder Precipitated in Different pH

ORIGINALITY REPORT

13%

SIMILARITY INDEX

6%

INTERNET SOURCES

9%

PUBLICATIONS

3%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|--|----|
| 1 | Submitted to Universitas Diponegoro
Student Paper | 3% |
| 2 | coek.info
Internet Source | 1% |
| 3 | Choudhury, Biswajit, and Amarjyoti Choudhury. "Lattice distortion and corresponding changes in optical properties of CeO ₂ nanoparticles on Nd doping", Current Applied Physics, 2013.
Publication | 1% |
| 4 | Lawrence Kumar, Pawan Kumar, Victor Kuncser, Simona Greculeasa, Balaram Sahoo, Manoranjan Kar. "Strain induced magnetism and superexchange interaction in Cr substituted nanocrystalline cobalt ferrite", Materials Chemistry and Physics, 2018
Publication | 1% |
| 5 | M.G. Sujana, K.K. Chattopadyay, S. Anand. "Characterization and optical properties of nano-ceria synthesized by surfactant- | 1% |

mediated precipitation technique in mixed solvent system", Applied Surface Science, 2008

Publication

6	ioc.tfbor.bg.ac.rs Internet Source	1 %
7	link.springer.com Internet Source	1 %
8	nopr.niscpr.res.in Internet Source	1 %
9	www.ciarte.pt Internet Source	1 %
10	www.mdpi.com Internet Source	1 %
11	Arshad Iqbal, Arham S. Ahmed, Nafees Ahmad, Tanveer Ahamad, Mohammad Zain Khan, Seema Srivastava. "Biogenic synthesis of CeO ₂ nanoparticles and its potential application as an efficient photocatalyst for the degradation of toxic amido black dye", Environmental Nanotechnology, Monitoring & Management, 2021 Publication	1 %
12	Ecco, L.G., M. Fedel, F. Deflorian, Jacob Becker, Bo Brummerstedt Iversen, and Aref Mamakhel. "Waterborne acrylic paint system	1 %

based on nanoceria for corrosion protection of steel", Progress in Organic Coatings, 2016.

Publication

13

Narottam Sutradhar, Apurba Sinhamahapatra, Sandip Pahari, Muthirulandi Jayachandran et al. "Facile Low-Temperature Synthesis of Ceria and Samarium-Doped Ceria Nanoparticles and Catalytic Allylic Oxidation of Cyclohexene", The Journal of Physical Chemistry C, 2011

Publication

1 %

14

Pourghahramani, P.. "Microstructure characterization of mechanically activated hematite using XRD line broadening", International Journal of Mineral Processing, 200605

Publication

1 %

15

repository.its.ac.id

Internet Source

1 %

16

Chen, H.I.. "Homogeneous precipitation of cerium dioxide nanoparticles in alcohol/water mixed solvents", Colloids and Surfaces A: Physicochemical and Engineering Aspects, 20040802

Publication

<1 %

17

Bhawana Jain, Ajaya K. Singh, Ayesha Hashmi, Md. Abu Bin Hasan Susan, Jean-Paul Lellouche. "Surfactant-assisted cerium oxide

<1 %

and its catalytic activity towards Fenton
process for non-degradable dye", Advanced
Composites and Hybrid Materials, 2020

Publication

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

Structural Analysis of Nanoceria Powder Precipitated in Different pH

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5
