

Feasibility of ceria nanocrystal adsorbent for amoxicillin removal from water

by Iis Nurhasanah

Submission date: 05-May-2023 02:09PM (UTC+0700)

Submission ID: 2084877746

File name: ria_nanocrystal_adsorbent_for_amoxicillin_removal_from_water.pdf (349.4K)

Word count: 2922

Character count: 16470

Feasibility of Ceria Nanocrystal Adsorbent for Amoxicillin Removal from Water

Iis Nurhasanah^{1,a*}, Kadarisman^b, Vincensius Gunawan^c and Heri Sutanto^d

¹Physics Department, Faculty of Mathematics and Sciences, Diponegoro University,
Jl. Prof. Soedarto, SH, Tembalang Semarang, Central Java, Indonesia 50275

^{a*}iisphysics@gmail.com, ^bkadarismanfisika@gmail.com, ^cgoenangie@gmail.com,

^dherisutanto@gmail.com

Keywords: ceria, adsorption, amoxicillin, adsorbent

Abstract. This study explored adsorptive property of ceria nanocrystal as an adsorbent for amoxicillin removal from water. Ceria nanocrystal was synthesized by employing precipitation method and characterized by using XRD and N₂ adsorption-desorption analysis. The adsorption experiment was performed by managing amoxicillin in natural condition. Then, parameters in the adsorption experiment, such as adsorbent dosage, contact time, temperature and initial concentration of amoxicillin are varied. The XRD pattern illustrated that the average crystallite size of ceria nanocrystal formation was 13.08 nm. N₂ adsorption-desorption analysis showed that ceria nanocrystal was mesoporous with specific surface area of 65.26 m²/g. The amoxicillin adsorption of ceria nanocrystal adsorbent was described by Langmuir isotherm model with maximum adsorption capacity of 37.17 mg/g. The adsorption kinetic of ceria nanocrystal corresponded to the pseudo-second order model. Removal efficiency of amoxicillin by ceria nanocrystal was approximately 80% within 60 minutes over temperature range 303-323K. Those parameter results are described that ceria nanocrystal adsorbent is feasible as a rapid amoxicillin removal from water.

Introduction

Cerium oxide (ceria), a rare earth oxide is commonly used as catalytic converters (automotive exhaust) [1], UV blocking agent (sunscreen) [2], and antioxidant agent (medicine) [3,4]. It is also used as an effective adsorbent for heavy metals and dyes pollutants removal in wastewater treatment [5, 6, 7, 8, 9, 10]. However, only a few studies explored the potential of ceria nanocrystal for antibiotic removal in water [11].

A very large usage of antibiotics contributes to water pollution resulted in bacterial resistance increment, and poses threat to ecosystem sustainability. One proposed method for handling antibiotics in water is the adsorption process using activated carbon [12-15]. Pourtedal and Sadegh showed that amoxicillin is the most difficult antibiotics to eliminate using activated carbon compared to other antibiotics such as cephalexin, tetracycline and penicillin [12]. The practical applications of activated carbon are still limited due to expensive raw material and complex manufacturing processes [16]. Therefore, exploration of alternative adsorbent for antibiotics removal continues.

Ceria in nanoscale sized (ceria nanocrystal) is favourable for pollutants adsorption in water due to large surface area and high mobility in solution. These properties enable a quick whole solution volume cleaning. This study described the feasibility of ceria nanocrystal as an adsorbent for amoxicillin removal. First, ceria nanocrystal was synthesized using precipitation method from relatively inexpensive cerium nitrate. Next, ceria nanocrystal was analysed using various models to determine kinetic parameters and mechanism of amoxicillin adsorption behaviour.

Experimental

Materials. Cerium nitrate hexahydrate (Ce(NO₃)₃·6H₂O) as cerium precursor was purchased from Sigma-Aldrich Ltd. Ammonium hydroxide (Merck) was used as precipitant. Demineralized

water (DW) and iso-propanol (Merck) were utilized as solvent. Amoxicillin was obtained from Indonesian Pharmaceutical.

Synthesis and characterization. Ceria nanocrystal was synthesized by precipitation method as described in reference [4]. Cerium nitrate solution (0.08 M) was made by dissolving cerium nitrate with mixed solvent of DW and iso-propanol. Ammonium hydroxide was added into solution until pH 10 was achieved. The precipitate was dried at 373K for 3 hrs and calcined at 773K for 2 hrs to form crystalline of ceria nanocrystal. The structure of ceria nanocrystal was analysed using X-ray diffractometer (PANalytical). The average crystallite size (D) and microstrain (η) were estimated using Williamson-Hall equation as [10]

$$\frac{\beta \cos \theta}{\lambda} = \frac{0.9}{D} + 4\eta \frac{\sin \theta}{\lambda} \quad (1)$$

Where λ is x-ray wavelength, β denotes FWHM, and θ is diffraction angle. Specific surface area (SSA) and pore size distribution were calculated from the N_2 adsorption/desorption using multipoint Brunauer-Emmett-Teller (BET) and Barret-Joyner-Halendra (BJH) method (Quantachrome Nova Instrument), respectively.

Adsorption experiment. The adsorption isotherm of amoxicillin was carried out with 20 mL amoxicillin solution (50 mg/L) and different amount of ceria nanocrystal (3 - 20 mg) to obtain optimum dosage of adsorbent. The mixture was stirred with the speed rotation of 300 rpm at room temperature in the dark condition. Experiment was performed for 60 min at pH ~ 5 as a natural condition of amoxicillin solution. Thus, adsorption equilibrium experiment was conducted with 15 mg of ceria nanocrystal and various concentration of amoxicillin solution (25-150 mg/L). For adsorption kinetic study, the experiment was taken with interval time 15-120 min in 50 mg/L amoxicillin solution. The samples were centrifuged at 6000 rpm for 10 min to separate adsorbent from solution. The residual of amoxicillin concentration was measured using UV-vis spectrophotometer (UV Vis 1240 Shimadzu) at 228 nm. In order to investigate the effect of temperature, adsorption experiment was performed in 50 mg/L amoxicillin solution at temperature 303, 313 and 323K. The removal efficiency η (%) of amoxicillin and adsorption capacity at contact time (t) of ceria nanocrystal were calculated using equations as follow:

$$\eta (\%) = \frac{(C_o - C_e)}{C_o} \times 100\% \quad (2)$$

$$q_t = \frac{(C_o - C_t)V}{m} \quad (3)$$

Where C_o (mg/L) and C_e (mg/L) represent the initial and equilibrium concentration of amoxicillin, C_t (mg/L) and q_t (mg/g) are concentration of amoxicillin and adsorption capacity at time (t), V (L) is volume of amoxicillin solution and m (g) denotes the mass of ceria nanocrystal.

Results and Discussion

Characterization of ceria nanocrystal. Figure 1(a) provides the XRD pattern of ceria nanocrystal. The identified diffraction peaks correspond to the cubic fluorite structure of cerianite (JCPDS:43-0394) which was consistent with other studies [4-10]. The size and microstrain were estimated using Williamson-Hall plot as shown in the insert of Fig 1(a). The obtained crystallite size was 13.08 nm and microstrain was 3×10^{-3} indicating the formation of ceria nanocrystal. N_2 adsorption/desorption isotherm measurement was used to calculate specific surface area and pore size of ceria nanocrystal. Fig. 1(b) exhibits hysteresis loop of N_2 adsorption/desorption isotherm of ceria nanocrystal. Based on the International Union of Pure and Applied Chemistry (IUPAC), the hysteresis loop identified as a type IV isotherm of mesoporous materials. The pore size distribution

(insert in Fig. 1(b)) shows pore size of ceria nanocrystal in the range 1.66 – 62.16 nm. In addition, three peaks at 2.31 nm, 3.46 nm and 6.30 nm observed, which shows the existence of mesoporous in ceria nanocrystal. The analysis of BET specific surface area indicated that ceria nanocrystal possessed $S_{\text{BET}} = 65.26 \text{ m}^2/\text{g}$ which is comparable to other research findings [9].

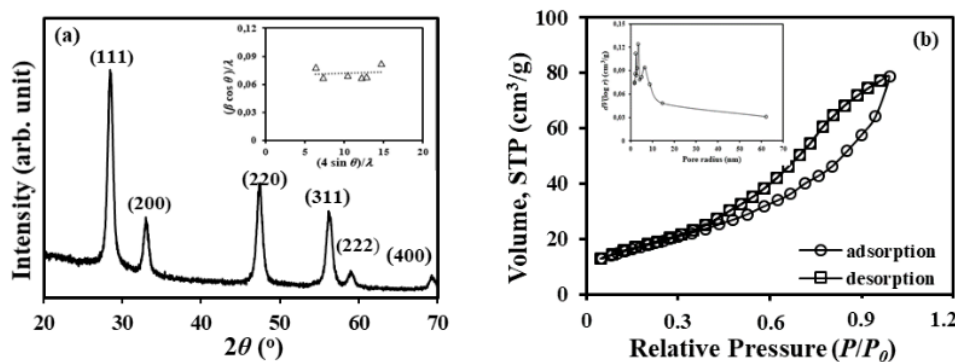


Fig. 1. (a). X-ray diffraction pattern and Williamson-Hall plot, (b). N_2 adsorption-desorption isotherm and the pore size distribution of ceria nanocrystal

Removal efficiency. The removal efficiency of amoxicillin for ceria nanocrystal with dosage of 3, 5, 10, 15 and 20 mg calculated using Eq.2. Fig. 2(a) depicts that removal efficiency of amoxicillin is risen as the amount of ceria nanocrystal is increased. The ceria nanocrystal amount of 15 mg yielded approximately 80% of the removal efficiency of amoxicillin. This result is higher than removal efficiency of amoxicillin using activated carbon [12]. The enhancement of ceria nanocrystal amount caused increase in surface area as active sites for adsorption [18]. Hence, it leads to the increment of adsorbed amoxicillin. However, the amount of ceria nanocrystal more than 15 mg did not result in an increase in removal efficiency. Hence, in this study 15 mg ceria nanocrystal was optimum dosage for adsorption of amoxicillin. In addition to the adsorbent dosage, temperature is also one of the parameters that affect removal efficiency. The removal efficiency of amoxicillin of about 80% achieved at temperature of 303, 313 and 323K as shown in Fig. 2(b). The temperature is insignificant affected on the removal efficiency. Similar result found on Cr(IV) adsorption on ceria nanosphere synthesized by hydrothermal process [6].

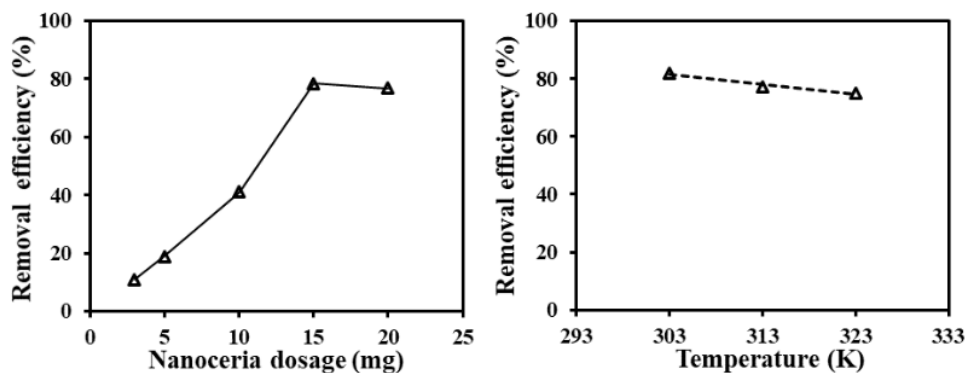


Fig. 2. Removal efficiency of amoxicillin for (a). Different ceria nanocrystal dosage, and (b). Different temperature (amoxicillin concentration 50 mg/mL, contact time 60 minutes)

Adsorption equilibrium. The adsorption equilibrium of amoxicillin on ceria nanocrystal surface was investigated based on removal efficiency which calculated for various contact time

from 15 to 120 min by using Eq. 2. Fig. 3 exhibits the removal efficiency of amoxicillin as function of contact time. The adsorption process resulted in 52% removal efficiency of amoxicillin in the first 15 min. The removal efficiency increased up to approximately 80% in 60 min and then almost unchanged up to 120 min. The result showed that the adsorption rate rises rapidly at the beginning and increases moderately within 15 to 60 min. Finally, the adsorption rate increases slightly until 120 min contact time. The equilibrium achieved in 60 min indicating rapid adsorption of amoxicillin on ceria nanocrystal surface.

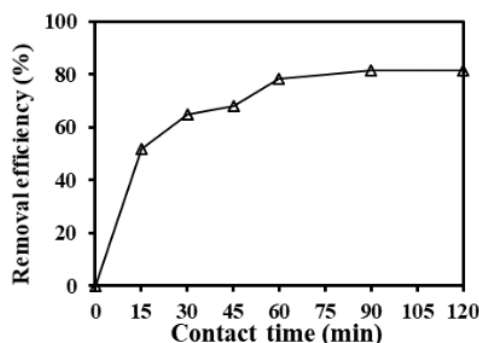


Fig. 3. Removal efficiency of amoxicillin versus contact time (amoxicillin concentration 50 mg/mL)

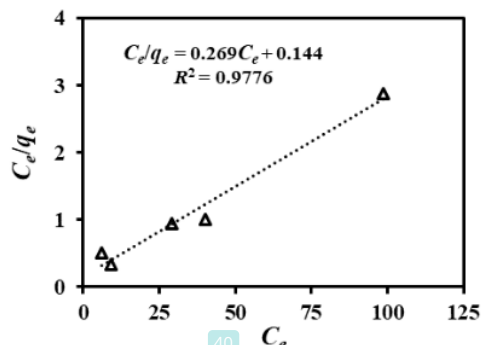


Fig. 4. Linear plot of Langmuir isotherm model for adsorption of amoxicillin on ceria nanocrystal

Adsorption isotherm. The adsorption experimental data fitting was performed to realize the application of ceria nanocrystal as an adsorbent for water pollutant treatment. Different adsorption isotherm models i.e. Langmuir, Freundlich, Temkin and Sips isotherm are mainly used to obtain suitable model that describes adsorption of amoxicillin on adsorbents [12-14,17]. In our study, adsorption of amoxicillin on ceria nanocrystal fitted well by Langmuir isotherm model. The linear form of Langmuir isotherm model represented as:

$$\frac{C_e}{q_e} = \frac{1}{q_m K_L} + \frac{C_e}{q_m} \quad (4)$$

Where q_m (mg/g) is the maximum adsorption capacity, K_L (L/mg) is the Langmuir isotherm constant. The linear plot of Langmuir isotherm model for adsorption of amoxicillin on ceria nanocrystal shown in Fig. 4. The Langmuir parameters (q_m and K_L) were obtained from the slope and the intercept of the vertical axis (Fig. 4). The value of q_m was found to be 37.18 mg/g which was closed to experimental data 39.96 mg/g, and the value of K_L was 0.187 (L/mg) with correlation coefficient (R^2) of 0.9776. The Langmuir isotherm model assumes monolayer adsorption on homogeneous sites [12-14]. Hence, the high value of correlation coefficient suggests that amoxicillin govern monolayer adsorbed on homogeneous surface of ceria nanocrystal. In addition, the feasibility of adsorption process determined by the essential isotherm characteristic of Langmuir model (R_L),

$$R_L = \frac{1}{1 + K_L C_o} \quad (5)$$

The value of R_L determines the nature of adsorption process. The nature of adsorption is unfavourable if $R_L > 1$, linear if $R_L = 1$, favourable if $0 < R_L < 1$ or irreversible if $R_L = 0$. The calculated R_L value using Eq. 5 was 0.097. Based on the value of R^2 and R_L , our ceria nanocrystal is feasible for amoxicillin removal from water [12-14].

Adsorption kinetic. The adsorption kinetic represents the relation of adsorption capacity and contact time. The experimental data fitted using the adsorption kinetic models: the pseudo-first order, pseudo-second order and intra-particle diffusion model [12-15,17]. The fitting of experimental data corresponded to pseudo-second order model. The linear form of pseudo-second order model expressed by:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{1}{q_e} t \quad (6)$$

Where k_2 denotes the equilibrium rate constant of pseudo-second order (g/mg.min). The plot of Eq. 6 depicted in Fig. 5(a). The result shows correlation coefficient (R^2) closed to 1, suggesting that the experimental data is in a good agreement with the pseudo-second order model. The adsorption parameters obtained from the slope and intercept of the linear plot in Fig. 5(a). The value of equilibrium adsorption capacity (q_e) was 30.58 mg/g closes to the value of experimental data (27.61 mg/g). Meanwhile, the adsorption rate constant was 8.52×10^{-2} (g/mg.min). The adsorption rate constant is an important parameter to evaluate feasibility and efficiency of adsorbents. These results show that pseudo-second order is an appropriate model to describe adsorption mechanism of amoxicillin on ceria nanocrystal [5,8,12-14].

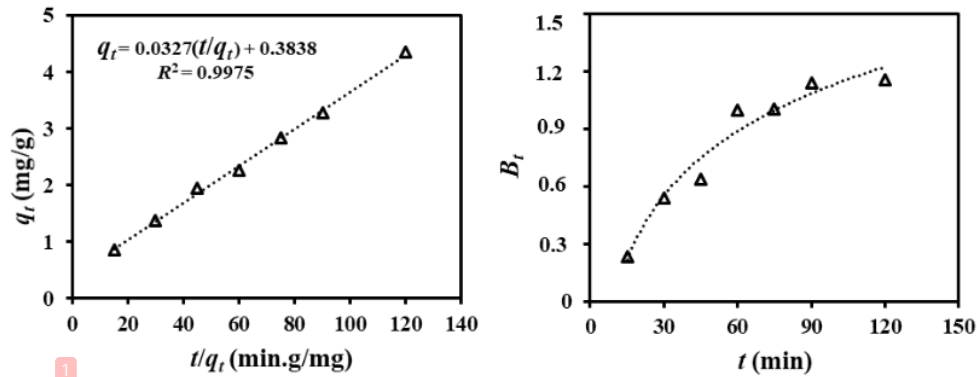


Fig. 5. (a). Pseudo-second order plot and (b). B_t vs t plot for adsorption of amoxicillin on ceria nanocrystal

Furthermore, the adsorption behaviour of amoxicillin on ceria nanocrystal was analysed to identify the embroiled mechanism in adsorption process. Two possible mechanisms that affect the rate-controlling adsorption process of amoxicillin on ceria nanocrystal are film and particle diffusion. The adsorption diffusion model applied to recognize whether film diffusion or particle diffusion that controlled adsorption rate [18].

$$B_t = -\ln(1 - F) - 0.4799 \quad (7)$$

$$F = \frac{q_t}{q_e} \quad (8)$$

Here, parameter F represents the fractional attainment of equilibrium at time t . The value of B_t was calculated for each F value using Eq.7. Fig. 5(b) shows the plot of B_t vs t for adsorption of amoxicillin on ceria nanocrystal. In the case B_t vs t plot is linear and passes through the origin, the adsorption process is dominated by particle diffusion. If the B_t vs t plot is non-linear, the adsorption process is controlled by film diffusion [18]. As can be seen in Fig. 5(b) the obtained B_t vs t plot is non-linear indicating that rate-controlling process is film diffusion.

Summary

This study investigated the adsorption properties of ceria nanocrystal which feasible to be applied for amoxicillin removal from water. The results reveal that the adsorption of amoxicillin on ceria nanocrystal well described by Langmuir isotherm with maximum adsorption capacity of 37.18 mg/g. The adsorption kinetic of amoxicillin on ceria nanocrystal, which controlled by film diffusion, corresponds to the pseudo second order kinetic model. The high removal efficiency of amoxicillin obtained for ceria nanocrystal dosage of 15 mg at temperature range 303-323K. However, further research is required to determine other adsorption parameters, such as pH so that a higher efficiency obtained.

Acknowledgments

We acknowledge the financial support from The Ministry of Research, Technology and Higher Education of Indonesia with contract number: 125/SP2H/PTNBH/DRPM/2018.

References

- [1] X. Zheng, Y. Li, L., Zhang, L. Shen, Y. Xiao, Y. Zhang, C. Au, L. Jiang, Insight into the effect of morphology on catalytic performance of porous CeO₂ nanocrystal for H₂S selective oxidation, Appl. Catal. B-Environ. 252 (2019) 98–110.
- [2] K. Anupriya, E. Vivek, B. Subramanian, Facile synthesis of ceria nanoparticles by precipitation route for UV blockers, J. Alloys Compd. 590 (2014) 406–410.
- [3] D. Gil, J. Rodriguez, B. Ward, A. Vertegel, V. Ivanov, V. Reukov, Antioxidant activity of SOD and Catalase Conjugated with Nanocrystalline Ceria, Bioeng. 4 (2017) 1–9.
- [4] I. Nurhasanah, W. Safitri, T. Windarti, A. Subagio, The calcination temperature effect on the antioxidant and radioprotection properties of CeO₂ nanoparticles, Reaktor. 18 (2018) 22–26.
- [5] H. Wang, Y. Zhong, H. Yu, P. Aprea, S. Hao, High efficiency adsorption for acid dyes over CeO₂ · xH₂O synthesized by a facile method, J. Alloys Compd. 776 (2019) 96–104.
- [6] J. Sun, C. Wang, L. Zeng, P. Xu, X. Yang, J. Chen, X. Xing, Q. Jin, R. Yu, Controllable assembly of CeO₂ micro/nanospheres with adjustable size and their application in Cr(IV) adsorption, Mater. Res. Bull. 75 (2016) 110–114.
- [7] P. Ji, J. Zhang, F. Chen, M. Anpo, Study of adsorption and degradation of acid orange 7 on the surface of CeO₂ under visible light irradiation, Appl. Catal. B 85(2009) 148–154.
- [8] S. Recillas, J. Colon, E. Casals, E. Gonzalez, V. Puentes, A. Sanchez, X. Font, Chromium VI adsorption on cerium oxide nanoparticles and morphology changes during process, J. Hazard. Mater. 184 (2010) 425–431.
- [9] Q. Feng, Z. Zhang, Y. Ma, X. He, Y. Zhao, Z. Chai, Adsorption and desorption characteristics of arsenic onto ceria nanoparticles, Nanoscale Res. Lett. 7/84 (2012) 1–8.
- [10] M.A.M. Khan, W. Khan, M. Ahamed, A.N. Alhazaa, Microstructural properties and enhanced photocatalytic performance of Zn doped CeO₂ nanocrystals, Sci. Rep. 7 (2017) 12560.
- [11] M. Brigante, P.C. Schulz, Adsorption of the antibiotic minocycline on cerium (IV) oxide: Effect of pH, ionic strength and temperature, Microporous Mesoporous Mater. 156 (2012) 138–144.
- [12] H.R. Pouretedal, N. Sadegh, Effective removal of amoxicillin, cephalexin, tetracycline and penicillin G from aqueous solution using activated carbon nanoparticles prepared from vine wood, J. Water Process Eng. 1 (2014) 64–73.

-
- [13] M.A. Chayid, M.J. Ahmed, Amoxicillin adsorption on microwave prepared activated carbon from *Arundo donax* Linn: Isotherms, kinetics, and thermodynamics studies, *J. Environ. Chem. Eng.* 3 (2015) 1592–1601.
- [14] O. Pezoti, A.L. Cazetta, K.C. Bedin, L.S. Souza, A.C. Martins, T.L. Silva, O.O. Santos Junior, J.V. Visentainer, V.C. Almeida, NaOH-activated carbon of high surface area produced from guava seeds as a high-efficiency adsorbent for amoxicillin removal: Kinetic, isotherm and thermodynamic studies, *Chem. Eng. J.* 288 (2016) 778–788.
- [15] L. Sellaoui, E.C. Lima, G.L. Dotto, A.B. Lamine, Adsorption of amoxicillin and paracetamol on modified activated carbons: Equilibrium and positional entropy studies, *J. Mol. Liq.* 234(2017) 375–381.
- [16] M.B. Ahmed, J.L. Zhou, H.H. Ngo, W. Gao, Adsorptive removal of antibiotics from water and wastewater: Progress and challenges, *Sci. Total. Environ.* 532 (2015) 112–126.
- [17] O. Kerkez-Kuyumcu, S.S. Bayazit, M.A. Salam, Antibiotic amoxicillin removal from aqueous solution using magnetically modified graphene nanoplatelets, *J. Ind. Eng. Chem.* 36 (2016) 198–205.
- [18] S. Aydin, M.E. Aydin, F. Beduk, A. Ulvi, Removal of antibiotics from aqueous solution by using magnetic Fe_3O_4 /red mud-nanoparticles, *Sci. Total Environ.* 670 (2019) 539–546.

Feasibility of ceria nanocrystal adsorbent for amoxicillin removal from water

ORIGINALITY REPORT

25%

SIMILARITY INDEX

18%

INTERNET SOURCES

22%

PUBLICATIONS

9%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|---|-----|
| 1 | real-phd.mtak.hu
Internet Source | 1 % |
| 2 | Minyoung Kim, Neha Sharma, Jiwon Chung, Kyusik Yun. "Activated graphene with fractal structure for the adsorption of malachite green with high removal rate", Microporous and Mesoporous Materials, 2021
Publication | 1 % |
| 3 | mdpi-res.com
Internet Source | 1 % |
| 4 | people.utm.my
Internet Source | 1 % |
| 5 | linknovate.com
Internet Source | 1 % |
| 6 | Wang, Ya, Lin Zhu, Haitao Jiang, Fang Hu, and Xiangqian Shen. "Application of longan shell as non-conventional low-cost adsorbent for the removal of cationic dye from aqueous solution", Spectrochimica Acta Part A | 1 % |

Molecular and Biomolecular Spectroscopy, 2016.

Publication

7	Submitted to Curtin University of Technology Student Paper	1 %
8	koreascience.or.kr Internet Source	1 %
9	ejournal2.undip.ac.id Internet Source	1 %
10	repository.maranatha.edu Internet Source	1 %
11	Lin Tian, Gang Xie, Rong-xing Li, Xiao-hua Yu, Yan-qing Hou. "Removal of Cr (VI) from aqueous solution using MCM-41", Desalination and Water Treatment, 2012 Publication	1 %
12	Madhumita Bhaumik, Shilpi Agarwal, Vinod Kumar Gupta, Arjun Maity. "Enhanced removal of Cr(VI) from aqueous solutions using polypyrrole wrapped oxidized MWCNTs nanocomposites adsorbent", Journal of Colloid and Interface Science, 2016 Publication	1 %
13	Michael C. Connelly, J.A. Sekhar. "U. S. energy production activity and innovation", Technological Forecasting and Social Change, 2012	1 %

14 Tan, I.A.W.. "Equilibrium and kinetic studies on basic dye adsorption by oil palm fibre activated carbon", Chemical Engineering Journal, 20070301 1 %
Publication

15 Zhihao AN, Wenwen ZHANG, Jingying MA, Ke ZENG, Ming YUAN, Donghui CHEN. "Adsorption of Azo Dye on Magnetically Separable Fe₃O₄/CeO₂ Nanocomposite: Kinetics, Isotherm, Mechanism", Materials Science, 2021 1 %
Publication

16 www.ijesd.org 1 %
Internet Source

17 Mambo Moyo, George Nyamhere, Edith Sebata, Upenyu Guyo. "Kinetic and equilibrium modelling of lead sorption from aqueous solution by activated carbon from goat dung", Desalination and Water Treatment, 2014 <1 %
Publication

18 Sanghamitra Kundu, A. K. Gupta. "Sorption Kinetics of As(V) with Iron-Oxide-Coated Cement–A New Adsorbent and its Application in the Removal of Arsenic from Real-Life Groundwater Samples", Journal of <1 %

Environmental Science and Health, Part A, 2005

Publication

19

hal.univ-lorraine.fr

Internet Source

<1 %

20

www.dovepress.com

Internet Source

<1 %

21

mail.scialert.net

Internet Source

<1 %

22

"Low Cost Adsorbents for Sustainable Dye Containing-Wastewater Treatment", Asian Journal of Chemistry, 2014.

Publication

<1 %

23

downloads.hindawi.com

Internet Source

<1 %

24

Minakshi Gohain, Pritam Bardhan, Khairujjaman Laskar, Saswati Sarmah et al. "Rhodotorula mucilaginosa: A source of heterogeneous catalyst for biodiesel production from yeast single cell oil and waste cooking oil", Renewable Energy, 2020

Publication

<1 %

25

Zhike Wang, Cunling Ye, Xueyuan Wang, Juan Li. "Adsorption and desorption characteristics of imidazole-modified silica for chromium(VI)", Applied Surface Science, 2013

Publication

<1 %

26 Zhu, R.. "Removal of Cd²⁺ from aqueous solutions by hydroxyapatite", Catalysis Today, 20081215 <1 %
Publication

27 repository.wima.ac.id <1 %
Internet Source

28 stars.library.ucf.edu <1 %
Internet Source

29 www.science.gov <1 %
Internet Source

30 Hao Zhou, Zhe Zhao. " The Preparation, Characterization and Photocatalytic Activity of Fe Ce O Microstructures ", Integrated Ferroelectrics, 2015 <1 %
Publication

31 Imran Ali. "New Generation Adsorbents for Water Treatment", Chemical Reviews, 2012 <1 %
Publication

32 Jiamin Yu, Yan Kang, Wenjun Yin, Jinlin Fan, Zizhang Guo. "Removal of Antibiotics from Aqueous Solutions by a Carbon Adsorbent Derived from Protein-Waste-Doped Biomass", ACS Omega, 2020 <1 %
Publication

33 Mirna Habuda-Stanić, Marija Nujić. "Arsenic removal by nanoparticles: a review", <1 %

34

Morshed Farokhi, Arsalan Parvareh, Mostafa Keshavarz Moraveji. "Adsorption optimization of Cr(VI) and Co(II) onto the synthesized chitosan/cerium oxide/iron oxide nano-composite in water system using RSM according to CCD method", DESALINATION AND WATER TREATMENT, 2019

Publication

<1 %

35

Qiang Liu, Bingsi Liu, Qinze Liu, Rongnian Xu, Hong Xia. "Lattice substitution and desulfurization kinetic analysis of Zn-based spinel sorbents loading onto porous silicoaluminophosphate zeolites", Journal of Hazardous Materials, 2019

Publication

<1 %

36

Zhang, Yongxing, Yingjie Ye, Zhongliang Liu, Bing Li, Qinzhuang Liu, Qiangchun Liu, and Xuanhua Li. "Monodispersed hierarchical aluminum/iron oxides composites micro/nanoflowers for efficient removal of As(V) and Cr(VI) ions from water", Journal of Alloys and Compounds, 2016.

Publication

<1 %

37

assets.researchsquare.com

Internet Source

<1 %

38	bibliotecadigital.udea.edu.co Internet Source	<1 %
39	d.researchbib.com Internet Source	<1 %
40	etd.aau.edu.et Internet Source	<1 %
41	ethesis.nitrkl.ac.in Internet Source	<1 %
42	www.nanoctr.cas.cn Internet Source	<1 %
43	www.researchsquare.com Internet Source	<1 %
44	Muhammad Raziq Rahimi Kooh, Linda B.L. Lim, Lee Hoon Lim, J.M.R.S. Bandara. "Batch adsorption studies on the removal of malachite green from water by chemicallymodified ", Desalination and Water Treatment, 2015 Publication	<1 %
45	N.A. Oladoja, A.E. Ofomaja, J.A. Idighe, A.K. Akinlabi, E.E. Egbon. "Sorption of Cu (II) ion from aqueous solution by scrap tyre", Desalination and Water Treatment, 2012 Publication	<1 %
46	Zong Hu, Xiaofei Liu, Dongmei Meng, Yun Guo, Yanglong Guo, Guanzhong Lu. "Effect of	<1 %

Ceria Crystal Plane on the Physicochemical and Catalytic Properties of Pd/Ceria for CO and Propane Oxidation", ACS Catalysis, 2016

Publication

47

Kalavathy, M.H.. "Kinetic and isotherm studies of Cu(II) adsorption onto H³PO⁴-activated rubber wood sawdust", Journal of Colloid And Interface Science, 20051215

Publication

<1 %

48

Rim Ben Arfi, Sarra Karoui, Karine Mouglin, Cyril Vaultot, Ludovic Josien, Gautier Schrodj, Laure Michelin, Achraf Ghorbal. "Enhanced Malachite Green uptake using chemically-modified reed-based powder: equilibrium, kinetics, mechanism, and reusability", International Journal of Environmental Analytical Chemistry, 2020

Publication

<1 %

49

Sari, A.. "Equilibrium, kinetic and thermodynamic studies of adsorption of Pb(II) from aqueous solution onto Turkish kaolinite clay", Journal of Hazardous Materials, 20071022

Publication

<1 %

50

Xu, J.. "Synergy effect on a suspended mixture of ceria and activated carbon for the photocatalytic degradation of phenol", Powder Technology, 20110610

Publication

<1 %

Exclude quotes Off

Exclude bibliography On

Exclude matches Off

Feasibility of ceria nanocrystal adsorbent for amoxicillin removal from water

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7