

Modification of Synthetic Zeolite from Bagasse Ash and Their Characterization

by Sriatun Sriatun

Submission date: 25-May-2019 09:28AM (UTC+0700)

Submission ID: 1135658342

File name: ynthetic_Zeolite_from_Bagasse_Ash_and_Their_Characterization.pdf (899.95K)

Word count: 2708

Character count: 14629

Modification of Synthetic Zeolite from Bagasse Ash and Their Characterization

Sriatun^a, Taslimah^a, Linda Suyati^a

Abstract

The modification used NH_4Cl and NiCl_2 salts to synthetic zeolite as a product of synthesis bagasse ash has been done. Several characterizations such as X-ray diffractometer and FTIR were done on the product of synthesis, whereas XRF and DTA-TGA were done on the product of modification. The FTIR spectra shows the product synthesis has main peaks of finger print of zeolite, meanwhile from the XRD pattern shows sharp peak which high intensity which means the sample has crystalline structure. The XRF analysis result showed that the silica was slightly reduced in modification with NH_4Cl . But silica decreased about 26 % when the zeolite was modified with NiCl_2 . from DTA data was known that on modification of zeolite with NH_4Cl , the endothermic zone was shifted from 104.3 -16.6 °C to 62.2-142.0 °C. The modification of zeolite with NiCl_2 the endothermic zone was shifted from 104.3 -16.6 °C to 39.3-106.8 °C. Meanwhile TGA data showed that all products had a thermal stability at temperature above 320 °C.

Keywords: modification, synthetic zeolite, Bagasse, Characterization

^a Chemistry Department, Science and Mathematics Faculty, Diponegoro University

Corresponding author e-mail address: sriatun71@gmail.com

Introduction

Milling process of sugar cane to obtain molasses always leaves about 35-40% of bagasse (Indriani and Sumiarsih in Anwar, 2008) or 32 % (P3GI, 2008). Meanwhile it has known that ash of bagasse contains high silica. Based on result's Hanafi and Nandang (2010), the content of silica on bagasse ash was 64.5 %, whereas in Aida (2010) was 70.9%. Both of them were considered as a proper potential to upgrade of the economic value of bagasse ash. It means the bagasse ash were converted to the more useful synthetic zeolite.

Research on the synthesis of material were carried out by Kondrashova et al (2010). He has synthesized silica using tetra ortho silicate (TEOS) as a source of silica and cetyltrimethylammonium bromide (CTAB) as a pore directing agent. The process of synthesis was conducted at various of heating time that was 3, 24 and 48 hours. Ertan et al (2009) have been producing silica (SiO_2) using sodium silicate as a source of silica, cetyltrimethylammonium bromide as a pore directing agent and heating time of 6, 24 and 72 hours. Wijayanti and Ediaty (2010) have synthesized MCM-41, Khan et al (2010) have synthesized Zeolite-A. Meanwhile Utchariyajit et al (2010) have synthesized SAPO-5 where silica powder as source of Si, and $\text{Al}(\text{OH})_3$ as source of Al, triethylamine (TEA) surfactant as pore forming agent. Yoon et al (2008) have synthesized organosilica.

In this research has been synthesized zeolite using bagasse ash as source of silica. On the process of synthesis required alkaline condition to obtain the materials target. The pH of solution should be higher than 10. It could be adjusted by means of adding NaOH solution. This led to the synthesis of products containing high sodium. The quality of product could be improved through modifications by using salt ammonium chloride (NH_4Cl) and nickel chloride (NiCl_2). Ammonium chloride was selected as the agent of the modifier because (1) it was easy to replace sodium ion, (2) if ammonium was heated at temperature above 350 °C, therefore it would be decomposed into ammonia gas and H^+ ion. Exactly, this formation gave us an advantage since the acidity of materials would increase. The addition of NiCl_2 salt into materials product also increased the acidity.

Methodology

Synthesis of zeolite from bagasse ash

Bagasse from sugar factory was dried then burned until the charcoal was formed. Furthermore the charcoal was calcined for 4 hours at 700 °C. Amount of 96 grams of ash measuring 100 mesh was reacted with NaOH 6 M. The mixture was stirred for 24 hours, then filtered. The filtrate was sodium silicate solution. The next step, sodium silicate was reacted with sodium aluminate. The volume ratio between sodium silicate and sodium aluminate was 1:1. The mixture was rapidly stirred at room temperature until gelatinous

materials were formed. Furthermore gelatinous materials were heated at 100 °C during 3 days. The obtained product was dried and characterized by FTIR (Fourier Transform Infrared), XRD (X-ray Diffraction).

Modification on Synthesized Zeolite by NH₄Cl and NiCl₂

There were two modification procedures to synthesized zeolite (1) synthetic zeolite was added NH₄Cl 2 M then shaken for 24 hours, filtered and dried, the last procedure for this step was calcined at 350 °C to remove NH₃ gas so only H⁺ which remains in modified materials. (2) Synthesized zeolite was added NiCl₂ 10% using impregnation method. The mixture was shaken for 24 hours at room temperature, then the solvent was evaporated. Furthermore, the modified materials were dried and calcined at 500 °C, so NiO or Ni would be formed in the materials. Finally, the properties of modified materials were characterized by XRF (X-ray Fluorescence), SEM (Scanning Electron Microscope), surface area analyser and DTA-TGA (Differential thermal analysis-Thermogravimetric analysis)

Results and Discussion

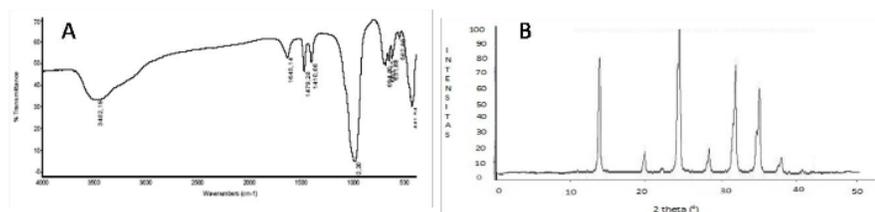


Figure 1. Characterization of synthesized zeolite (A) FTIR spectra (B) XRD Diffractogram

Modification of synthesized zeolite by NH₄Cl

The modification process aims to substitute Na⁺ ion by NH₄⁺ in synthesized zeolite. Indeed, substitution might occur at several other cations, so not only on the Na⁺ ion. Ammonium ion (NH₄⁺) was selected as a cation exchange to Na⁺ because it has high selectivity, i.e. NH₄⁺ > Ag⁺ > Ba²⁺ > Na⁺ > Sr²⁺ > Ca²⁺ > Li⁺ > Cu²⁺ (Tsitsishvili et al, 1992). In addition, NH₄⁺ ion easy to form acidic zeolite (H-zeolite) because the heating at 350 °C, NH₄⁺ was decomposed and released NH₃ gas so it formed H-zeolite. Physically, there were not any changing on both of colour and texture of synthesized and modified zeolite.

Modification of synthesized zeolite by NiCl₂

This process used NiCl₂ as a precursor, because it was known that NiCl₂ has trans esterification catalytic activity. The NiCl₂ precursor was loaded into synthesized zeolite by the way impregnation method.

The using of NaOH on the extraction process of silica from bagasse ashes caused it contains an assortment of metals oxides, meanwhile NaOH more selective to silica. Aqueous solution of NaOH was also used in the preparation of sodium aluminate. The high concentration of NaOH caused the solution were extremely alkaline. This condition was suitable for the synthesis process of zeolite because Si₄O₈(OH)₄⁴⁻ and Al(OH)₄⁻ anions would be appears in solution. Those anions would interacted to form silica alumina polymers as a zeolite material. So they had an important role play in the rate of growth of crystal nuclei (Hamdan, 1992).

FTIR spectra showed that Si-O-Al or Si-O-Si frameworks has been formed at wavenumber 992 cm⁻¹. It is an asymmetric stretching vibration. The following peaks are asymmetric stretching vibration at 663 cm⁻¹, double ring at 562 cm⁻¹, bending vibration of T-O at 441 cm⁻¹, and may pore opening.

Based on XRD data revealed that the obtained product has a crystal structure. This was showed by the advent of high intensity peaks which were the main peaks at 2θ = 24.58; 14.11 and 31.91 which have an intensity 23110 counts, 18470 counts and 17276 counts respectively.

This way was expected more effective because there was no NiCl₂ was wasted. The concentration of precursor solution was 10%. We could observed that white colour of synthesized zeolite has been changed to light blue colour on modified zeolite by NiCl₂.

The increasing of amount of NiCl₂ which was loaded into surface of supported materials/synthesized zeolite led to the surface area of materials also increased. The large of surface area has an important role in raising the catalytic activity.


The formation of NiO crystals from solution containing Ni²⁺ ion covers several stages. First, dissolving the NiCl₂ crystal into the aquadest causing the occurrence of hydrolysis of NiCl₂·6H₂O.



Hydrolysis reaction of Ni²⁺ ion would generated active catalytic site as a Brønsted acid.



The next step, ion Ni^{2+} was converted to NiO by heating process. We consider that the calcination temperature at 450 °C spurred the forming of covalent bonding between Ni and O. Nickel has empty d orbital that very potential as active catalytic site.



Lewis acid as an active catalytic site

Characterization modified zeolite by XRF

This characterization aims to know the elements/components containing in materials. Characterization was also done to bagasse ashes as starting material. Below is a table of the constituent components of the synthesized and modified zeolite.

From table, it is known that the ash from bagasse contains 27.7 % of silica, 28.9% K as alkali components, 20.1% Ca as earth alkali component and 10% Fe, 2.35% Mn as other components. Therefore the ash from bagasse can be used as a source of silica in synthesis silica alumina material like zeolite. In this materials, the ratio of Si/Al of synthesized zeolite was 1.67, other components such as K, Ca and Fe decline significantly. This indicates that on the extraction process of silica only few components that are involved in extraction by NaOH. It means that the NaOH is an exactly effective extraction agent.

The modification of zeolite by NH_4Cl 2 Mg gave H-zeolite, however the constituent component only slightly changed, therefore the ratio of Si/Al appears constant. In spite, the striking changes was observed when modification by NiCl_2 , synthesized zeolite changed to Ni-zeolite. The content of Si and Al reduced to 17.3% and 14%, but the percentage of Ni increases until 58.35%, whereas content of other component decline. The high nickel content in Ni-zeolite indicated that the NiCl_2 precursor is an effective loading agent.

Table 1. Constituent components of the synthesized and modified zeolite

Component (%)	Type of Materials			
	Ash	Zeolite before modification	Modified Zeolite by NH_4Cl	Modified Zeolite by NiCl_2
Si	27.7	44.1	43.0	17.3
Al	0	26.2	25.9	14
P	3.1	1.1	0.77	0.2
K	28.9	2.1	2.2	0.41
Ca	20.1	3.59	3.49	0.66
Ti	0.64	0.45	0.4	0.077
Mn	2.35	0.15	0.14	-
Fe	10.0	0.85	0.83	0.29
Ni	1.99	3.55	2.99	58.35

Characterization of modified zeolite by SEM

This characterization aims to find out the surface morphology, particle shape and size homogeneity. Figure 1 shows surface morphology of synthesized zeolite, H-zeolite and Ni-zeolite. The shape and size of the particles on the synthesized zeolite have similarities to the H-zeolite. The diameter of the particles approximately 1.5 μm . However, in H-zeolite more homogeneous because there's only a few of the small square particles and there is a lot more empty space. It means the treatment on the synthesized zeolite by NH_4Cl could create a homogeneity.

In the meantime, it seems clear that there is a fine grains on the surface of Ni-zeolite materials. It was suspected as nickel oxide/nickel which supported into the synthesized zeolite. In addition, the size of particles increased to approximately 2 μm .

Characterization of modified zeolite by BET surface Area Analyser

Characterization by BET aims to establish of pore size, pore volume and surface area a solid materials. Besides that, we could know the differences in material porosity before and after modification process.

Table 2 shows the increasing of surface area after modification process by NH_4Cl and NiCl_2 . The raising of surface area is 9 times. This happens on modified zeolite by NiCl_2 because a lot of NiO crystal adhered on the surface of particles. This result relevant with SEM photo where there is other smaller particles on the surface particles.

Table 2. The surface area, pore volume and pore radius of synthesized and modified zeolite

Material	Synthesized Zeolite (before modification)	Modified Zeolite by NH_4Cl	Modified Zeolite by NiCl_2
Surface area (m^2/g)	13.5	17.15	116.99
Pore volume (cc/g)	5.1×10^{-3}	6.48×10^{-3}	4.6×10^{-2}
Pore radius Size (Å^*)	1.8	1.8	1.83

Average pore radius of synthesized and modified zeolite were not change, they were about 1.8 Å . The pore volume of Ni-zeolite was slightly decline, it is thought to be due to NiO was accumulated on pore/channel and covered up of the surface of pore, or it might be occurred agglomeration.

Characterization of Modified Zeolite by DTA-TGA (Differential Thermal Analysis - Thermogravimetric Analysis)

The purpose of DTA characterization find out the thermal property and phase changing materials as an effect of enthalpy changing. The materials would be decomposed if it was heated at high temperature. Decomposition of materials was observed as DTA curve. That is a plot of temperature function versus time. Consider that the decomposition reaction is affected by other species, the ratio of size and volume, matter composition (Bukit, 2012).

Thermogravimetric analysis (TGA) is characterization to determine the thermal stability and fraction of volatile components by the way calculated the weight changing that correlated with temperature changing. Some properties of thermogravimetric are (1) horizontal part/flat indicated no weight changing (2) wrapped part indicated loss weight.

From DTA data in figure 3, modification treatment has been replaced endothermic zone from 104.3 -165.6 °C to 62.2-142.0 °C by NH_4Cl and 39.3-106.8 °C by NiCl_2 .

Furthermore thermogram TGA shows all of the product had thermal stability at temperature ≥ 320 °C.

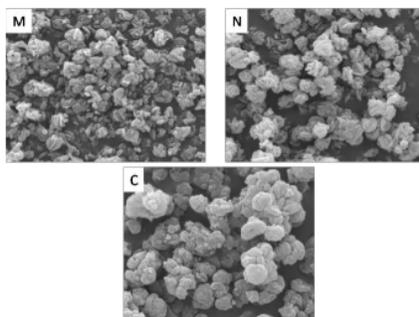


Figure 2. The SEM photographs at magnitude 20.000 x (M) synthesized zeolite/before modification, (H) Modified zeolite by NH_4Cl , (C) Modified zeolite by NiCl_2

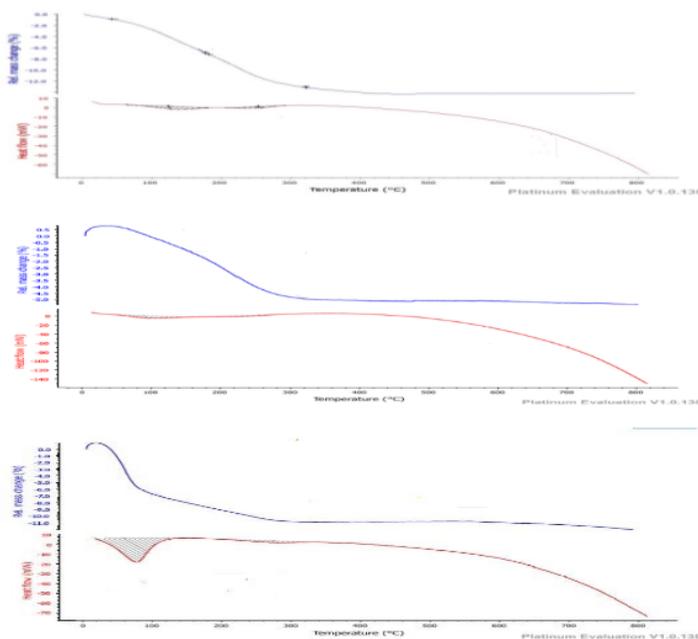


Figure 3. DTA-TGA curve (A) synthesized zeolite (B) Modified zeolite by NH_4Cl (C) Modified Zeolite by NiCl_2

Conclusions

Based upon the results and discussion, we got any conclusion that modification using NH_4Cl and NiCl_2 salt could improve the properties/characters of

synthesized zeolite. This characters included the content of constituent component, performance of surface, surface area and thermal stability. The characters just a slightly increased if using NH_4Cl but very tangible on using NiCl_2 .

1

Proceedings of
The 9th Joint Conference on Chemistry

ISBN 978-602-285-049-6

Acknowledgements

This research is financially supported by DITLITABMAS DIKTI

References

3

Aida N, Dewanti L., 2010, Pembuatan Silika Gel Dari Abu Ampas Tebu Dengan Proses Ekstraksi Basa (NaOH) dan Sol Gel, *Tugas Akhir*, Institut Teknologi Sepuluh November.

Anwar, Syaiful, 2008, Ampas Tebu, *Skripsi Fakultas Teknik Pertanian*, Universitas Brawijaya, Malang.

7

Bukit, N., 2012, Mechanical and Thermal Properties of Polypropylene Reinforced by Calcined and Uncalcined Zeolite, *Makara*, Vol. 16, No.2, 121-128.

Ertan, A, Kodumuri P, Orhan T, Tewari Surendra N, 2009, Effect of Synthesis Time and Traement on Porosity of Mesoporous Silica Materials, *Adsorption*, 15: 81-86.

5

Hanafi, A., Nandang, A., 2010, Studi Pengaruh Bentuk Silika dari Ampas Tebu terhadap Kekuatan Produk Keramik, *Jurnal Kimia Indonesia*, 5 (1), 35-38

4

Khan, A., Arafat, S., Reza, M., Razzaque, S., and Alam, M., 2010, Lynde Type-A Zeolite Synthesis and Effectof

Crystallization On Its Surface Acidity, *Indian Journal of Chemical Technology*, Vol.17, 303-308

Kondrashova, N.B, Le¹⁰eva, I.I., Saenko, E.V., and Val'tsifer V.A., 2010, Influence of the Temperature-Time Conditions on the Textural and Structural Properties of Mesoporous Silicon Dioxide Synthesized in An Ammonia-Alcohol Medium, *J. App. Chem* Vol. 83 No. 8, 1425-1428

2

Utcharyajit, K., and Wongkasemjit, S., 2010, Effect of Synthesis Parameters On Mesoporous SAPO-5 With AFI-type Formation Via Microwave Radiation Using Alumatrane and Silatrane Precursors, *Microporous and Mesoporous Materials*, Vol. 135, 116-123

6

Wiyanti, N.D., andEdiati, R., 2010, Sintesis MCM-41 Menggunakan Sumber Silika Dari Abu Layang Batubara PT. IPMOMI PAITON Dengan Variasi Komposisi Dan Waktu Hidrotermal, *Prosiding Skripsi*, Sepuluh Nopember Institute of Technology, Surabaya

9

Yoon, S.S., Son, W.J, Biswas, K., and Ahn, S.W., 2008, Synthesis of Periodic Mesoporous Organosilica by Microwave Heating, *Bull. Korean Chem. Soc.* 2008, Vol. 29, No. 3., 609-614

Modification of Synthetic Zeolite from Bagasse Ash and Their Characterization

ORIGINALITY REPORT

10%

SIMILARITY INDEX

7%

INTERNET SOURCES

5%

PUBLICATIONS

5%

STUDENT PAPERS

PRIMARY SOURCES

1	journal.uin-alauddin.ac.id Internet Source	2%
2	mafiadoc.com Internet Source	1%
3	www.scribd.com Internet Source	1%
4	Submitted to Universiti Teknologi Petronas Student Paper	1%
5	jurnal.ugm.ac.id Internet Source	1%
6	digilib.its.ac.id Internet Source	1%
7	iiste.org Internet Source	1%
8	"Synthesis of Periodic Mesoporous Organosilica by Microwave Heating", Bulletin of the Korean Chemical Society, 03/20/2008 Publication	1%

9

Paritosh Mohanty, Nyi Myat Khine Linn, Kai Landskron. "Ultrafast Sonochemical Synthesis of Methane and Ethane Bridged Periodic Mesoporous Organosilicas", Langmuir, 2010

Publication

<1%

10

Submitted to University of Petroleum and Energy Studies

Student Paper

<1%

11

Submitted to Higher Education Commission Pakistan

Student Paper

<1%

12

Suhartana, Emmanuella Sukmasari, Choiril Azmiyawati. "Modification of Natural Zeolite with Fe(III) and Its Application as Adsorbent Chloride and Carbonate ions", IOP Conference Series: Materials Science and Engineering, 2018

Publication

<1%

13

G Christidis. "Zeolitisation of perlite fines: mineralogical characteristics of the end products and mobilization of chemical elements", Applied Clay Science, 1999

Publication

<1%

14

www.publications.muet.edu.pk

Internet Source

<1%

15

docplayer.net

Internet Source

<1%

Exclude quotes Off

Exclude matches Off

Exclude bibliography Off