

# The Optimum Conditions of Carboxymethyl Chitosan Synthesis on Drug Delivery Application and Its Release of Kinetics Study

*by* Dwi Hudyanti

---

**Submission date:** 16-Nov-2019 06:14AM (UTC+0700)

**Submission ID:** 1214762778

**File name:** C6.\_the\_optimum\_condition.....pdf (527.64K)

**Word count:** 4805

**Character count:** 25810

## The Optimum Conditions of Carboxymethyl Chitosan Synthesis on Drug Delivery Application and Its Release of Kinetics Study

Parsaoran Siahaan<sup>1\*</sup>, Nadira Cahyaning Mentari<sup>1</sup>, Ustera Octovindra Wiedyanto<sup>1</sup>, Dwi Hudyanti<sup>1</sup>, Suci Zulaikha Hildayani<sup>1</sup>, and Marlyn Dian Laksitorini<sup>2</sup>

<sup>1</sup>Department of Chemistry, Diponegoro University, Jl. Prof. Soedarto Tembalang, Semarang 50277, Indonesia

<sup>2</sup>Department of Pharmaceutics, Faculty of Pharmacy, Universitas Gadjah Mada Sekip Utara, Yogyakarta 55281, Indonesia

Received April 21, 2017; Accepted July 7, 2017

### ABSTRACT

In this paper, carboxymethyl chitosan (CMC) was synthesized and studied as a carrier to encapsulate vitamin (as drug model) and controlled release. Chitosan (CS) is a polycationic derived from chitin, which suitable for active substance carrier system on biomedical function. CS has good properties such as non-toxic, biodegradable, and biocompatible. However, CS insoluble in an aqueous solvent so CS was modified chemically into CMC. CMC was formed by reacting CS and monochloroacetic acid with sodium hydroxide (NaOH) as a catalyst. Optimization was performed by varying the NaOH concentration during alkalinizing the CS and the temperature reaction. The functional group and crystallinity of CS and CMC were estimated by FTIR and XRD. The degree substitution of carboxymethylation has an average value of 0.60. The results show optimum temperature reaction and NaOH concentration were 60 °C and 40% (w/v). The nicotinamide (NA), a hydrophilic vitamin, was loaded within CMC matrix system through in vitro precipitation method. To confirm the encapsulation of NA in CMC and the release kinetics of NA from CMC in distilled water was studied through UV-Vis spectrophotometry. The release profile of NA from CMC matrix system carried out for 3 h and 12 h. The rate of NA release from CMC increases with increasing time and the follows a zero order, Higuchi, and Korsmeyer-Peppas kinetics rules.

**Keywords:** carboxymethyl chitosan; temperature reaction; NaOH concentration; encapsulation; release kinetics

### ABSTRAK

Dalam penelitian ini, karboksimetil kitosan (CMC) telah disintesis dan dipelajari sebagai pembawa untuk mengenkapsulasi vitamin (sebagai model obat) dan pelepasan terkontrol. Kitosan (CS) merupakan polikationik hasil deasetilasi kitin, yang cocok digunakan sebagai matriks pembawa zat aktif dalam bidang biomedis. CS bersifat tidak beracun, biodegradabel, dan biokompatibel. Namun, CS tidak larut dalam pelarut air sehingga CS dimodifikasi secara kimia menjadi CMC. CMC dibentuk dengan mereaksikan CS dan asam monokloroasetat dengan natrium hidroksida (NaOH) sebagai katalis. Optimasi dilakukan dengan memvariasikan temperatur reaksi dan konsentrasi NaOH selama alkalisasi CS. Gugus fungsi dan kristalinitas dari CS dan CMC dianalisis dengan FTIR dan XRD. Derajat substitusi (DS) tingkat karboksimetilasi memiliki nilai rata-rata 0,60. Hasil penelitian menunjukkan temperatur optimum dan konsentrasi NaOH yaitu 60 °C dan 40% (w/v). Nikotinamida (NA) merupakan vitamin hidrofilik yang dienkapsulasi dalam sistem matriks CMC melalui metode presipitasi in vitro. Enkapsulasi NA di CMC dan kinetika pelepasan NA dari CMC dalam air destilasi dipelajari melalui spektrofotometri UV-Vis. Profil pelepasan NA dari sistem matriks CMC dilakukan selama 3 dan 12 jam. Laju pelepasan NA dari CMC meningkat dengan bertambahnya waktu dan mengikuti aturan kinetika orde nol, Higuchi dan Korsmeyer-Peppas.

**Kata Kunci:** karboksimetil kitosan; temperatur reaksi; konsentrasi NaOH; enkapsulasi; kinetika pelepasan

### INTRODUCTION

Over the past several decades, many scientists have focused their attention on the development of ideal drugs that specifically target the site of action. Synthesis of drug loaded polymer particles has attracted extensive attention due to the protection function and controlled

release properties of the particles. The drug can be either incorporated by passive absorption or chemical conjugation into the carrier matrix. An example of a natural polymer that can be used as a carrier matrix of the active substance is chitosan. Chitosan is usually preferred as carrier matrix because of its biocompatibility, biodegradability, and non-toxicity [1-7].

\* Corresponding author; Tel : +62-81310553498  
Email address : parsaaoran\_s@undp.ac.id

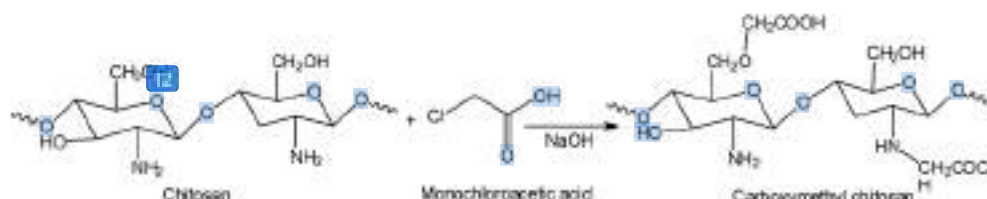


Fig 1. Reaction of Carboxymethyl Chitosan Formation

Chitosan (CS) or  $\beta$ -D-(1,4)-glucosamine is cationic polysaccharide main derivative of chitin which is from the shells of crustaceans, so it is available very abundant in nature [8-13]. Chitosan insoluble in neutral and alkaline pH because of the amino groups of chitosan are weak bases which predominantly protonated when  $\text{pH} < 6.5$  and it very stable crystalline structure arising from strong hydrogen bonds [14]. Therefore, the solubilization of chitosan only dilutes in acid solutions. So the poor solubility of chitosan when  $\text{pH} > 6.5$  is a serious drawback in many of its applications, especially as a drug carrier matrix. However, chitosan has reactive amino, primary hydroxyl, and secondary hydroxyl groups which can be used for chemical modification under mild reaction condition to overcome its limited solubility in aqueous media [15-16]. Many water soluble chitosan derivatives have been prepared by introducing hydrophilic groups, such as carboxymethyl groups. CMC has a higher solubility than chitosan in the neutral solvent due to the hydrophilic groups. This advantage makes CMC widely used in various fields: food industry, agriculture, cosmetic, biomedicine, and pharmaceutical [17-20].

Carboxymethyl chitosan (CMC) can be made through the alkylation process by using sodium hydroxide (NaOH) and reacted with the monochloroacetic acid ( $\text{ClCH}_2\text{COOH}$ ) as depicted in Fig. 1, thus forming carboxymethyl groups on the chitosan polymer chain. Some factors that influence CMC forming are the ratio of water: isopropyl alcohol, the degree of deacetylation (DD), temperature reaction and alkaline concentration (NaOH) [14,21]. The increase of the ratio water: isopropyl alcohol decrease the fraction of carboxymethylation. The increase of the temperature reaction will increase the fraction of carboxymethylation [17]. The degree of substitution (DS) carboxymethyl groups strongly dependent on NaOH concentration used. NaOH aqueous solution as a catalyst. The employment of high NaOH concentration promoted side reaction between NaOH and chloroacetic acid and the available chloroacetic concentration for the reaction decreased accordingly [14].

In biomedical function, CMC used as carrier matrix in encapsulation system. Encapsulation is one of the quality preservation techniques of sensitive substances and a method for production of materials with new valuable properties [22]. The encapsulation technique of

choice depends on the type and physical properties of the core and shell material. Different methods have been used to encapsulation. Selection of any of the methods depends on factors such as particle size requirement, the thermal and chemical stability of the active agent, reproducibility of the release kinetic profiles, the stability of the final product and residual toxicity associated with the final product [23]. Some methods of encapsulation are emulsion cross-linking, emulsion-droplets coalescence, ionotropic-gelation, precipitation, reverse micelles, a sieving method, spray drying [24]. Precipitation is quite methods. Particles are produced by blowing polymer solution into an alkali solution like sodium hydroxide [23].

Encapsulation is a phenomenon of intermolecular interaction. Chitosan has lower encapsulation efficiency than CMC due to its hydrophobicity. In this paper, chitosan is modified into CMC to improve the encapsulation efficiency and release kinetics. Encapsulation efficiency between chitosan and CMC was determined by nicotinamide (NA) as drug model [25-26]. Rate release of nicotinamide from matrix system will be determined by slow release kinetics mechanism [27-30].

## EXPERIMENTAL SECTION

### Materials

Materials used in this study were chitosan with a degree of deacetylation 71.90%, sodium hydroxide (Merck), monochloroacetic acid (Merck), and nicotinamide (Sigma Aldrich). All chemical and reagents used in this experiment were of analytical grade.

### Instrumentation

The instruments in this experiment were glass tools Pyrex © Iwaki<sub>TC-12</sub> made in Thailand, analytical balance KERN ALS 220-4N made in Germany, oven Fisher Scientific model 630F made in USA, filter paper Whatman<sup>®</sup> Schleicher and Schuell 110 mm made in England, thermometer, hotplate and magnetic stirrer, pH meter Handylab Schott, HANNA conductometer model H1991300 made in Romania, Hettich centrifuges

EBA 20 made in Germany, Shimadzu FTIR Spectrometer made in Japan, UV Vis 1601 Spectrophotometer model T60 U made in Germany and Shimadzu XRD-7000 made in Japan.

## Procedure

### Preparation of carboxymethyl chitosan

Chitosan (40 g) was dispersed in 20 mL of isopropanol and stirring for 20 min at room temperature. Next 5 mL of aqueous NaOH was added than 45 min stirring and 12 g of monochloroacetic acid was then added to the suspension. The reaction proceeded to the 3 h with temperature, 40 °C, 50 °C, 60 °C, 70 °C, 80 °C, 90 °C, and 100 °C for each mixture. Then the solid product was then filtered, suspended in 100 mL methanol. The product was dried at 60 °C in an oven for 12 h and finally in a vacuum desiccators at room temperature. FTIR used to structural characterization.

Different carboxymethyl chitosan samples was prepared by employing different temperature reaction (room temperature /CMC-A, 40 °C/CMC-B, 50 °C/CMC-C, 60 °C/CMC-D, 70 °C/CMC-E, 80 °C/CMC-F, 90 °C/CMC-G, and 100 °C/CMC-H for each mixture) and concentration of NaOH (20%/CMC-D1, 30%/CMC-D2, 40%/CMC-D3, 50%/CMC-D4, 60%/CMC-D5, 70%/CMC-D6, and 80%/CMC-D7 (w/v) for each mixture).

### Solubility and conductivity test

A 100 mg CMC was inserted into a glass beaker and 20 mL double distilled water was added to it slowly to dissolve of the carboxymethyl chitosan completely. After 1 h, carboxymethyl chitosan remaining separated by vacuum drying. Then the residue has dried to determine the amount of mass loss in dissolved water. The conductivity was tested every 10 min during 1 h. The solubility and conductivity were testing at room temperature.

$$\text{Carboxymethyl chitosan solubility (\%)} = \frac{M_i - M_f}{M_i} \times 100 \quad (1)$$

$M_i$  = initial mass of carboxymethyl chitosan (g)

$M_f$  = final mass of carboxymethyl chitosan (g)

### Degree of substitution

Worked by de Abreu et al. [31], the degree of substitution was determined by automatic titrator (Schott Titronic Universal) with an accuracy of 0.05 mL. In our lab we did not have these instruments, so we follow Rahmawati et al. [32] method, the degree of substitution (DS) of this carboxymethyl chitosan was calculated following the equation (2).

A 100 mg of CMC in 10 mL of 0.12 M NaOH was prepared. The mixture is stirred 30 min at room temperature. Methyl red as an indicator was added and

the mixture was titrated with 0.13 M HCl until the mixture became reddish.

$$DS = \frac{MW \times M \times (B - S)}{1000 \times W} \quad (2)$$

MW = molecular weight of monomer chitosan (g/mol)

B = volume of HCl blank (mL)

S = volume of HCl sample (mL)

M = molarity of HCl (mol/L)

W = mass of sample (g)

DS = number of substituted hydroxyl group

### Characterization of chitosan and carboxymethyl chitosan

FTIR and XRD were used to the characterization the functional groups and crystallinity of CS and CMC.

### Encapsulation efficiency and nicotinamide (NA) release

Encapsulation was done on 500 mg of CS and CMC. The samples were dissolved in 1% acetic acid. Then the sample solution was added by 40 mL NA 2500 ppm and stirring for 5 min. Furthermore, the mixture was precipitated by 1 N NaOH. The separation of encapsulated NA using a centrifuge at 5000 rpm for 30 min. The filtrate was subjected to spectrometric measurement at 263 nm with UV Vis 1601 Spectrometer. The encapsulation efficiency was determined by:

$$\text{Encapsulation efficiency (\%)} = \left( \frac{C_{\text{of NA}} - C_{\text{f of NA}}}{C_{\text{of NA}}} \right) \times 100 \quad (3)$$

Fifty (50) mg of NA-CS and NA-CMC was added into 40 mL distilled water and the release was estimated at different time points. Three milliliters of the sample was taken at each time interval then analyzed in UV Vis 1601 Spectrometer to estimate the nicotinamide concentration at 263 nm.

Data obtained from *in vitro* release studies were fitted to various kinetics equations to discover the mechanism of drug release from prepared formulations. The kinetic models used were zero order, first order, Higuchi and Korsmeyer-Peppas models. The rate constants were also calculated for the respective models.

Zero order:

$$Q_t = Q_0 - k_0 t \quad (4)$$

where  $Q_t$  is the amount of drug dissolved at time  $t$ ,  $Q_0$  is initial drug concentration,  $k_0$  the kinetics constant.

First order:

$$\ln Q_t = \ln Q_0 + K_1 t \quad (5)$$

where  $k_1$  the constant rate of the first order.

Korsmeyer-Peppas model (eq.7) to explain drug release from the polymeric system:

$$M_t / M_\infty = K_1 t^n \quad (6)$$

where  $M_t/M_\infty$  is cumulative drug released at time  $t$ ,  $k$  the kinetics constant, and  $n$  the release exponent and determines the release mechanism.

Higuchi models (eq.8) used to study of drug release, either water soluble or slightly soluble in water, a polymeric matrix solid or semi-solid.

$$M_t / M_\infty = K_r \sqrt{t} \quad (7)$$

where  $K_r$  the kinetics constant

## RESULT AND DISCUSSION

### Synthesis of Carboxymethyl Chitosan

The aim of this study was to obtain the optimum condition for the synthesis of carboxymethyl chitosan with the highest solubility in water. Therefore, the various type carboxymethyl chitosan was made with various concentration of NaOH and temperature reaction. The works in the reference report that the carboxymethyl chitosan occurs selectively according to the conditions used in the reaction, a complex mixture of products is generally obtained when ordinary conditions are used. During carboxymethylation of chitosan with monochloro acetic acid in the mildly alkaline medium of pH  $\pm$  8, only

the amine groups will take place. The products result from variation in temperature can be seen in Fig. 2.

From varying the temperature of reaction (Fig. 2), it can be seen that the products have different color due to increasing temperature. CMC-A until CMC-D have the same color, but start from CMC-E to CMC-H have a darker color. According to Wijaya et al. [33], the chitosan TGA results that at 57.54–153.76 °C occurs water vaporing and followed by decomposition of chitosan. It proves that CMC-E to CMC-H has a different color. This prediction supported by solubility and conductivity test results (as shown in Fig. 3).

Based on the results, the optimum temperature of carboxymethyl chitosan synthesis at 60 °C (CMC-D) with solubility in water 43.50%.

After the optimum temperature was found then the optimum concentration of NaOH on the synthesis of carboxymethyl chitosan was determined. The products result from the various concentration of NaOH have the same color (Fig. 4) indicating that variation concentration of NaOH did not have impact physically property.

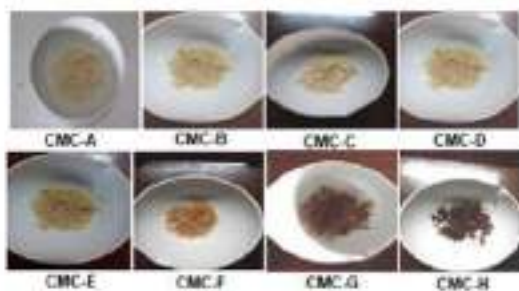


Fig 2. CMC varied by temperature

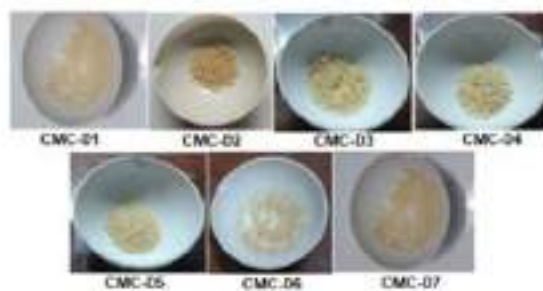


Fig 4. CMC varied by NaOH concentration

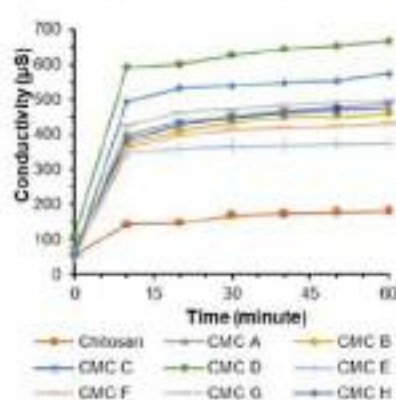
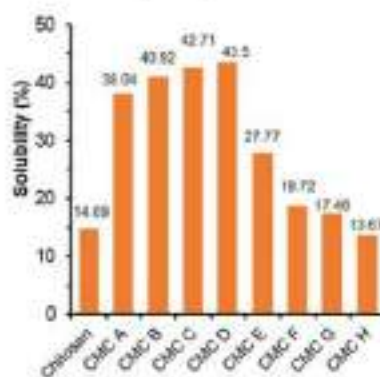


Fig 3. Solubility and conductivity test of chitosan and CMC varied by temperature

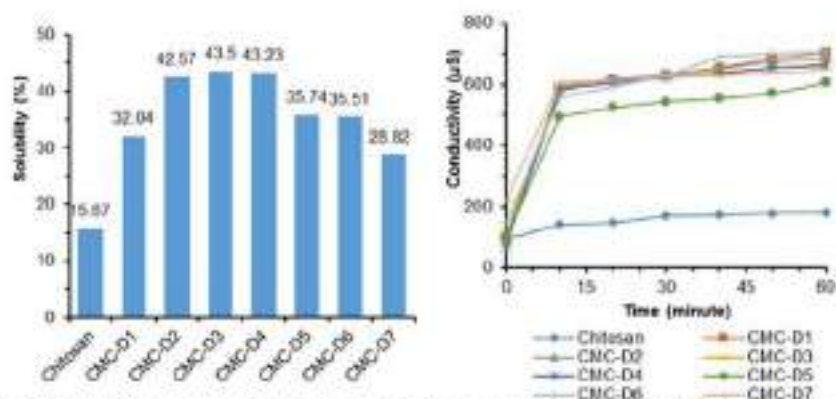


Fig 5. Solubility and conductivity test of chitosan and CMC varied by NaOH concentration

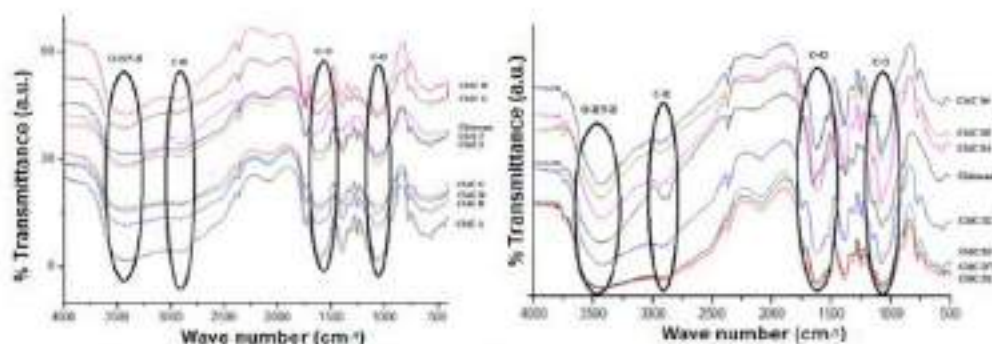


Fig 6. FTIR spectra of chitosan and CMC varied by temperature and varied by NaOH concentration

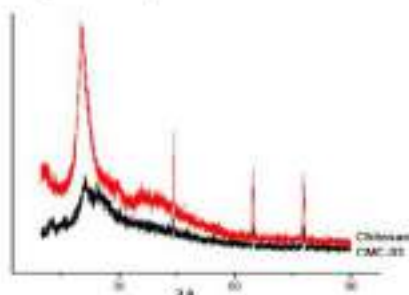


Fig 7. XRD diffractogram of chitosan and CMC-D3

Table 1. Value of DS carboxymethyl chitosan determined by titration

Sample	DS
CMC-D1	0.68
CMC-D2	0.69
CMC-D3	0.69
CMC-D4	0.67
CMC-D5	0.64
CMC-D6	0.62
CMC-D7	0.60

The degree of substitution (DS) strongly dependent on NaOH concentration used the value of DS as shown in Table 1. The rigid crystalline structure of chitosan was difficult to disrupt to ensure penetration of the monochloroacetic acid at lower concentration of NaOH into the interlocking polymer chains resulting in a lower degree of substitution. In contrast, employing a high concentration of NaOH promoted side reaction between NaOH and monochloroacetic acid and the available monochloroacetic concentration for reaction forming carboxymethyl chitosan reduced accordingly.

The DS value of the sample CMC-D3 and CMC-D2 (Table 1) are same, but the solubility of CMC-D3 higher than D2. It is indicated that the synthesis of carboxymethyl chitosan optimum with 40% (w/v) NaOH addition. The solubility and conductivity test results are shown in Fig. 5.

#### FTIR and XRD Study

The infrared absorption spectrum of chitosan and carboxymethyl chitosan are shown in Fig. 6. The specific

wavenumber  $3441\text{ cm}^{-1}$  shows OH and NH stretching vibration,  $2924\text{--}2854\text{ cm}^{-1}$  shows the CH stretching vibration, and  $1635\text{ cm}^{-1}$  shows the C=O bond, and  $1080\text{ cm}^{-1}$  for C-O bond [20]. The peaks that appear in the infrared spectrum of chitosan and carboxymethyl chitosan are identical in the infrared spectra of chitosan, the peak observed at a wavenumber  $3425.58\text{ cm}^{-1}$  is the stretching vibration of  $\text{OH}$  and  $\text{NH}$  groups. The peak at wavenumber  $1604.77\text{ cm}^{-1}$  in the bending vibration of  $\text{NH}_2$  group. The C-O stretching vibration at  $1080\text{ cm}^{-1}$ .

According to Mi et al. [19], the specific peaks of carboxymethyl chitosan at wavenumber  $1744\text{ cm}^{-1}$  (C=O of carboxylic acid),  $1608\text{ cm}^{-1}$  (stretching vibration of  $-\text{COO}^-$  antisymmetric of salt carboxylic), and  $1421\text{ cm}^{-1}$  (stretching vibration of  $-\text{COO}^-$  symmetric). Based on spectra FTIR of chitosan (Fig. 6), all carboxymethyl chitosan have specific peaks at wavenumber  $1743\text{ cm}^{-1}$ ,  $1620$  and  $1396\text{ cm}^{-1}$  both in temperature and concentration of NaOH variation. The based on Fig. 6 that carboxymethyl been formed.

Based on the obtained result of XRD diffractogram as depicted in Fig. 7, CS can be recognized with the emergence of the sharp characteristic peak at an angle of  $20^\circ$ , while CMC can be recognized by the appearance of the characteristic peak that is less sharp than CS at an angle of about  $33^\circ$  [34]. In this study, the characteristic peak of CS appears at an angle of

$20.6393^\circ$ , while the characteristic peak of CMC appears at an angle of  $32.9299^\circ$ . Based on XRD diffractogram, CS has crystalline structure while CMC has an amorphous structure. This difference of their structure proves that CMC more soluble than CS in water.

#### Encapsulation Efficiency and Nicotinamide Release

The encapsulation efficiency of NA-CS and NA-CMC was shown in the Fig. 8. Compared with the CS, the CMC yielded a higher EE. A possible explanation for this difference was that CMC possessed a hydrophilic group, which allowed for higher capacity of NA incorporation. This result shows that with more functional groups involved in the polymer-vitamin interaction [21]

The release of three samples at 3 h early in accordance with the 0-order kinetics with correlation coefficient  $>0.99$ . Kinetics of the 0-order on drug encapsulation system by using a controlled release polymer can be obtained. When the initial concentration of the drug beyond the solubility of the drug in the system and the concentration of the drug is constant. Drug release will be proceeded by the dissolution of the existing drug on the surface of the system and follow by swelling matrix polymer. The drug

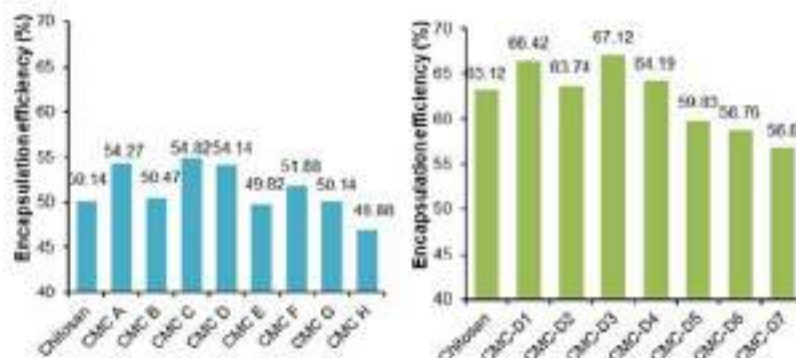


Fig 8. Encapsulation efficiency of chitosan and CMC

Table 2. Time release during 3 h

Kinetics Models	Parameters	Samples		
		Chitosan	CMC-D1	CMC-D3
0 Order	$R^2$	0.9917	0.1161	0.9926
	$k_0$	0.0336	0.9694	0.0689
1 <sup>st</sup> Order	$R^2$	0.9791	0.9818	0.9925
	$k_1$	0.0025	0.0016	0.0017
Korsmeyer-Peppas	$R^2$	0.9857	0.9789	0.9455
	$k_{kp}$	1.6252	1.3759	1.3906
	$n$	0.2108	0.1386	0.1432
Higuchi	$k_H$	0.0408	0.1338	0.0075
	$R^2$	0.9959	0.9958	0.9739

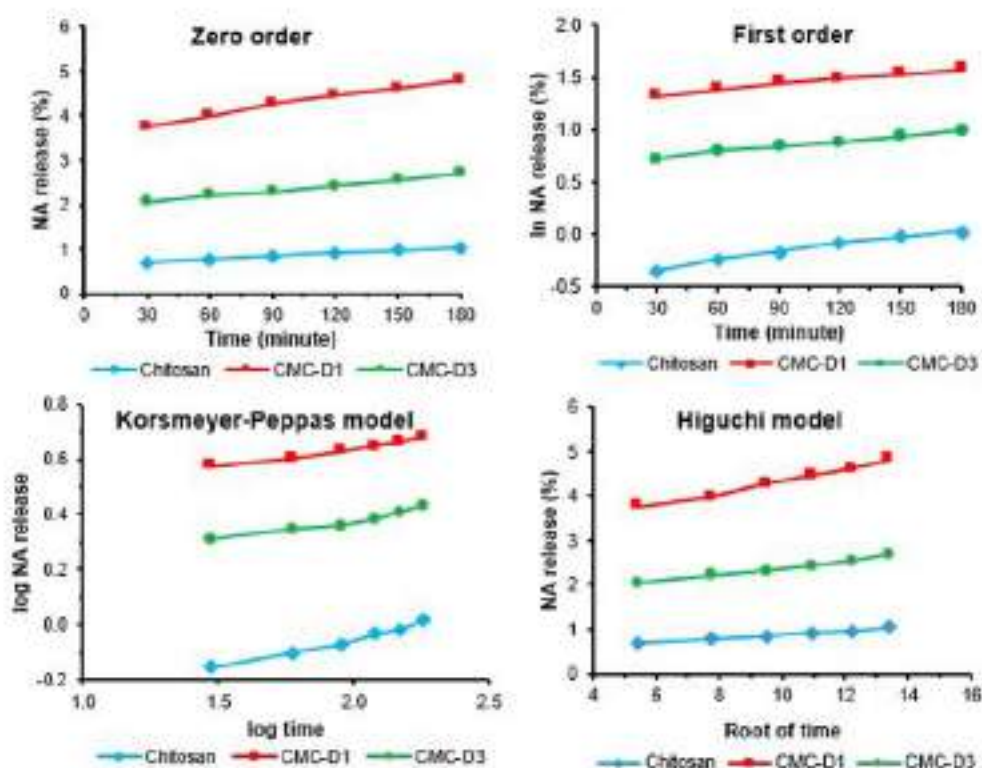


Fig 9. Time release during 3 h

Table 3. Time release during 12 h

Kinetics Models	Parameters	Samples		
		Chitosan	CMC-D1	CMC-D3
0 Order	$R^2$	0.9954	0.9970	0.9825
	$k_0$	0.5816	0.1390	0.3619
1 <sup>st</sup> Order	$R^2$	0.9908	0.9970	0.9851
	$k_1$	0.0269	0.0032	0.0089
Korsmeyer-Peppas	$R^2$	0.9671	0.9406	0.9016
	$k_{KP}$	1.4632	1.0406	1.1160
	$n$	0.1653	0.0173	0.0477
Higuchi	$k_H$	0.1810	0.0105	0.1043
	$R^2$	0.9911	0.9639	0.9524

in the deeper parts will come out of the system when the drug on the surface had separated, so the concentration increases [35].

The release profile of NA from NA-CS, NA-CMC-D1, and NA-CMC-D3 with respect to time can be shown in Table 2 and Fig. 9.

All of the samples follow 0-order kinetics. It is indicated drug release occurring at any given time is relatively constant, so the drug can last longer on the system. The drug concentration release from CMC higher than CS. This will lead to determining the amount

of the drug on the encapsulating system when designing long-term controlled release of the drug. Increasing concentration of drug release from CMC higher than CS because CMC more easily dissolve in water. So that the drug will more easily separate from CMC than CS matrix due to the interaction between water and hydrophilic groups of CMC.

A mathematical model that is also in accordance with the all of the sample drug release is Korsmeyer-Peppas and Higuchi with the correlation coefficient for each sample  $>0.97$ . Both of this model that has been



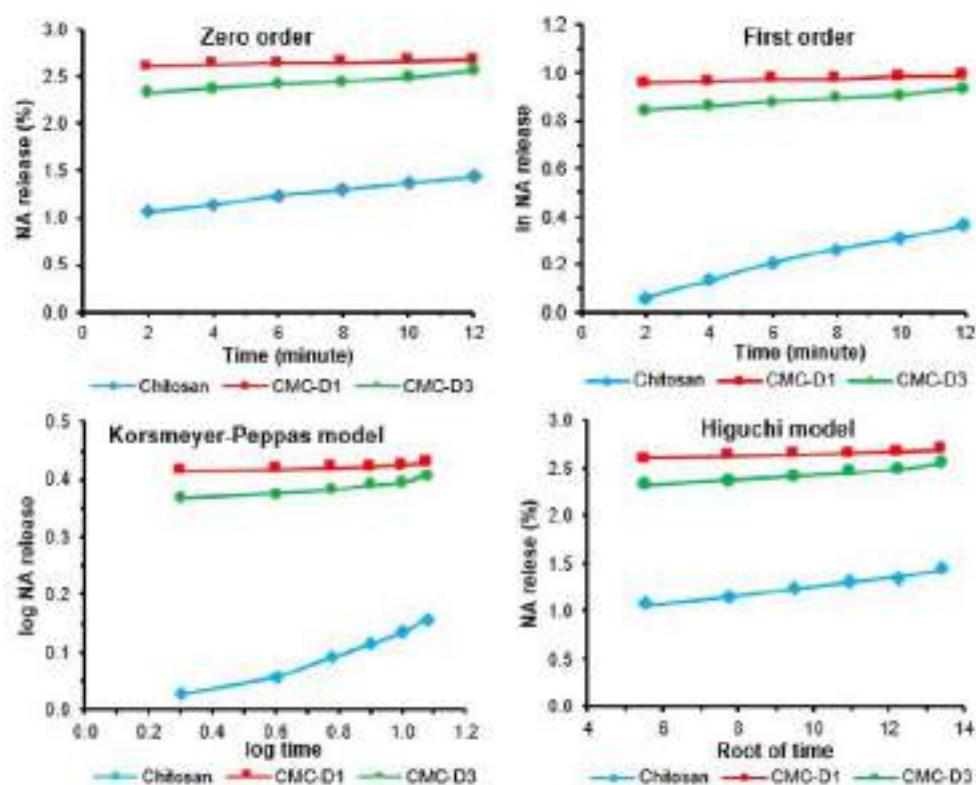


Fig 10. Time Release during 12 h

recognized and often used to determine the drug release mechanism. Drug release mechanism can be seen from the value of  $n$  resulted. The  $n$  value is between 0.13-0.21. It indicates that drug release mechanism is not only influenced by the drug diffusion process, but also degradation of the polymeric matrix. Based on these models can be estimated that the release process through 2 steps, (i) drug release fully caused by drug diffusion and (ii) the degradation of polymer matrix [35]. Determination of drug release of all samples was done in a longer time that is 12 hours to know the stability of the system as depicted in Table 3 and Fig. 10.

The based on Table 3 show that the accumulation of drug concentration release from CMC matrix higher than CS. During 12 h of drug release making the polymeric matrix unstable. According to the Korsmeyer-Peppas and Higuchi models, the  $n$  value and the correlation coefficient of 12 h drug release lower than 3 h.

The initial release of NA can be attributed to release of NA adsorbed onto the surface of CS and CMC matrix system. CMC-D3 had a slow release of

nicotinamide thus making CMC-D3 a potential candidate as matrix system of encapsulation.

## CONCLUSION

The optimum synthesis conditions of carboxymethyl chitosan obtained in this study are the use of temperature reaction at 60 °C and 40% (w/v) NaOH concentration for alkalizing chitosan respectively. The highest solubility in water of CMC-D3 is 43.50%. The encapsulation efficiency of NA-CMC-D3 is 67.12% and follows zero order kinetic model.

## ACKNOWLEDGEMENT

Thanks to Prof. Teruna J. Siahaan, Ph.D. (Pharmacy Department, University of Kansas, US), for the valuable direction and discussion of encapsulation and drug delivery systems. Thanks to the Directorate General of Higher Education. Last but not least Faculty of Science and Mathematics, which has funded this research through the Research Funding Scheme 2016.

## REFERENCES

- [1] Paniche, H., and Paniche, C., 2011, Chitosan nanoparticles: A contribution to nanomedicine, *Polym Int.*, 60 (6), 883–889.
- [2] Vemmer, M., and Patel, A.V., 2013, Review of encapsulation methods suitable for microbial biological control agents, *Biol. Control*, 67 (3), 380–389.
- [3] van der Lubben, I.M., Verhoef, J.C., Borchard, G., and Junginger, H.E., 2001, Chitosan for mucosal vaccination, *Adv. Drug Delivery Rev.*, 52 (2), 139–144.
- [4] Koppolu, B.P., Smith, S.G., Ravindranathan, S., Jayanthi, S., Suresh Kumar, T.K., and Zaharoff, D.A., 2014, Controlling chitosan-based encapsulation for protein and vaccine delivery, *Biomaterials*, 35 (14), 4382–4389.
- [5] Mizrahy, S., and Peer, D., 2012, Polysaccharides as building blocks for nanotherapeutics, *Chem. Soc. Rev.*, 41 (7), 2623–2640.
- [6] Siafaka, P.I., Titopoulou, A., Koukaras, E.N., Kostoglou, M., Kouris, E., Karavas, E., and Bikiris, D.N., 2015, Chitosan derivatives as effective nanocarriers for ocular release of timolol drug, *Int. J. Pharm.*, 495 (1), 249–264.
- [7] Cheng, X., Liu, R., and He, Y., 2010, A simple method for the preparation of monodisperse protein-loaded microspheres with high encapsulation efficiencies, *Eur. J. Pharm. Biopharm.*, 76 (3), 336–341.
- [8] Rinaudo, M., 2006, Chitin and chitosan: Properties and applications, *Prog. Polym. Sci.*, 31 (7), 603–632.
- [9] Ye, Z., Guo, J., Wu, D., Tan, M., Xiong, X., Yin, Y., and He, G., 2015, Photo-responsive shell cross-linked micelles based on carboxymethyl chitosan and their application in controlled release of pesticide, *Carbohydr. Polym.*, 132, 520–528.
- [10] Vakili, M., Rafatullah, M., Ibrahim, M.H., Abdullah, A.Z., Salamatinia, B., and Gholami, Z., 2016, Chitosan hydrogel beads impregnated with hexadecylamine for improved reactive blue 4 adsorption, *Carbohydr. Polym.*, 137, 139–146.
- [11] Kouchak, M., Avadi, M., Abbaepour, M., Jahangiri, A., and Boldaji, S.K., 2012, Effect of different molecular weights of chitosan on preparation and characterization of insulin loaded nanoparticles by ion gelation method, *Int. J. Drug Dev. Res.*, 4 (2), 271–277.
- [12] Berger, J., Reist, M., Mayer, J.M., Felt, O., Peppas, N.A., and Gurny, R., 2004, Structure and interactions in covalently and ionically crosslinked chitosan hydrogels for biomedical applications, *Eur. J. Pharm. Biopharm.*, 57 (1), 19–34.
- [13] Bernkop-Schnürch, A., and Dünnhaupt, S., 2012, Chitosan-based drug delivery systems, *Eur. J. Pharm. Biopharm.*, 81 (3), 463–469.
- [14] Mourya, V.K., Inamdar, N.N., and Tiwari, A., 2010, Carboxymethyl chitosan and its application, *Adv. Mater. Lett.*, 1 (1), 11–33.
- [15] Mourya, V.K., and Inamdar, N.N., 2009, Trimethyl chitosan and its applications in drug delivery, *J. Mater. Sci. - Mater. Med.*, 20 (5), 1057–1079.
- [16] Mourya, V.K., and Inamdar, N.N., 2008, Chitosan-modifications and applications: Opportunities galore, *React. Funct. Polym.*, 68 (6), 1013–1051.
- [17] Chen, L., Du, Y., and Zeng, X., 2003, Relationships between the molecular structure and moisture-absorption and moisture-retention abilities of carboxymethyl chitosan. II. Effect of degree of deacetylation and carboxymethylation, *Carbohydr. Res.*, 338 (4), 333–340.
- [18] Chen, L., Tian, Z., and Du, Y., 2004, Synthesis and pH sensitivity of carboxymethyl chitosan-based polyampholyte hydrogels for protein carrier matrices, *Biomaterials*, 25 (17), 3725–3732.
- [19] Mi, Y., Su, R., Fan, D.D., Zhu, X.L., and Zhang, W.N., 2013, Preparation of N,O-carboxymethyl chitosan coated alginate microcapsule and their application to *Bifidobacterium longum* BIOMA 5920, *Mater. Sci. Eng. C*, 33 (5), 3047–3053.
- [20] Teng, Z., Luo, Y., and Wang, Q., 2013, Carboxymethyl chitosan-soy protein complex nanoparticles for the encapsulation and controlled release of Vitamin D<sub>3</sub>, *Food Chem.*, 141 (1), 524–532.
- [21] Kurniasih, M., Purwati, P., Hermawan, D., and Zaki, M., 2014, Optimum conditions for the synthesis of high solubility carboxymethyl chitosan, *Malay. J. Fundam. Appl. Sci.*, 10 (4), 189–194.
- [22] Jyothi, N.V., Prasanna, P.M., Sakarkar, S.N., Prabha, K.S., Ramalah, P.S., and Srawan, G.Y., 2010, Microencapsulation techniques, factors influencing encapsulation efficiency, *J. Microencapsulation*, 27 (3), 187–197.
- [23] Agnihotri, S.A., Mallikarjuna, N.N., and Aminabhavi, T.M., 2004, Recent advances on chitosan-based micro- and nanoparticles in drug delivery, *J. Controlled Release*, 100 (1), 5–28.
- [24] Kashyap, P.L., Xiang, X., and Heiden, P., 2015, Chitosan nanoparticle based delivery systems for sustainable agriculture, *Int. J. Biol. Macromol.*, 77, 36–51.
- [25] Maiese, K., Chong, Z.Z., Hou, J., and Shang, Y.C., 2009, The vitamin nicotinamide: Translating into clinical nutrition care, *Molecules*, 14 (9), 3446–3485.

- [26] Lappas, M., and Permezel, M., 2011, The anti-inflammatory and antioxidative effects of nicotinamide, a vitamin B3 derivative, are elicited by FoxO3 in human gestational tissues: implications for preterm birth, *J. Nutr. Biochem.*, 22 (12), 1195–1201.
- [27] Aiping, Z., Jianhong, L., and Wenhui, Y., 2006, Effective loading and controlled release of camptothecin by O-carboxymethylchitosan aggregates, *Carbohydr. Polym.*, 63 (1), 89–96.
- [28] Souza, J.M., Caldas, A.L., Tchid, S.D., Molina, J., Souto, A.P., Fanguero, R., and Zille, A., 2014, Properties and controlled release of chitosan microencapsulated limonene oil, *Rev. Bras. Farmacogn.*, 24 (6), 691–698.
- [29] Mhlanga, N., and Ray, S.S., 2015, Kinetic models for the release of the anticancer drug doxorubicin from biodegradable poly(lactide)/metal oxide-based hybrids, *Int. J. Biol. Macromol.*, 72, 1301–1307.
- [30] Vaghani, S.S., Patel, M.M., Satish, C.S., Patel, K.M., and Jivani, N.P., 2012, Synthesis and characterization of carboxymethyl chitosan hydrogel: Application as site specific delivery for lercanidipine hydrochloride, *Bull. Mater. Sci.*, 35 (7), 1133–1142.
- [31] de Abreu, F.R., and Campana-Filho, S.P., 2009, Characteristics and properties of carboxymethylchitosan, *Carbohydr. Polym.*, 75 (2), 214–221.
- [32] Rahmawati, H., and Iskandar, D., 2014, Sintesis karboksimetil kitosan terhadap pengaruh konsentrasi natrium hidroksida dan rasio kitosan dengan asam monokloroasetat, *Jurnal Teknologi Technoscience*, 6 (2), 145–155.
- [33] Wijaya, H.G., Eko, S., and Lukman, A., 2010, Analisis termal gravimetri film gelatin komersial kitosan, *Prosiding Kimia FMIPA ITS*, 1–8.
- [34] Patale, R.L., and Patravale, V.B., 2011, O,N-Carboxymethyl chitosan-zinc complex: a novel chitosan complex with enhanced antimicrobial activity, *Carbohydr. Polym.*, 85 (1), 105–110.
- [35] Siepmann, J., and Peppas, N.A., 2011, Higuchi equation: derivation, applications, use and misuse, *Int. J. Pharm.*, 418 (1), 6–12.

# The Optimum Conditions of Carboxymethyl Chitosan Synthesis on Drug Delivery Application and Its Release of Kinetics Study

## ORIGINALITY REPORT

14%

SIMILARITY INDEX

5%

INTERNET SOURCES

11%

PUBLICATIONS

6%

STUDENT PAPERS

## PRIMARY SOURCES

1	<a href="https://www.mdpi.com">mdpi.com</a> Internet Source	1%
2	<a href="https://www.ncbi.nlm.nih.gov">www.ncbi.nlm.nih.gov</a> Internet Source	1%
3	N.T. An, P.L. Dung, D.T. Thien, N.T. Dong, T.T.Y. Nhi. "An improved method for synthesizing N,N'-dicarboxymethylchitosan", Carbohydrate Polymers, 2008 Publication	<1%
4	<a href="https://link.springer.com">link.springer.com</a> Internet Source	<1%
5	Mardiyah Kurniasih, Purwati, Thika Cahyati, Ratna Stia Dewi. "Carboxymethyl chitosan as an antifungal agent on gauze", International Journal of Biological Macromolecules, 2018 Publication	<1%
6	Submitted to Mahidol University Student Paper	<1%

7	Liping Sun, Yumin Du, Lihong Fan, Xiao Chen, Jianhong Yang. "Preparation, characterization and antimicrobial activity of quaternized carboxymethyl chitosan and application as pulp-cap", Polymer, 2006 Publication	<1%
8	Submitted to Higher Education Commission Pakistan Student Paper	<1%
9	Submitted to Indian Institute of Technology Roorkee Student Paper	<1%
10	Cheng, X.. "A simple method for the preparation of monodisperse protein-loaded microspheres with high encapsulation efficiencies", European Journal of Pharmaceutics and Biopharmaceutics, 201011 Publication	<1%
11	opac.wbut.ac.in Internet Source	<1%
12	kth.diva-portal.org Internet Source	<1%
13	unsri.portalgaruda.org Internet Source	<1%
14	Lingyun Chen, Yumin Du, Xiaoqing Zeng. "Relationships between the molecular structure	<1%

and moisture-absorption and moisture-retention abilities of carboxymethyl chitosan", Carbohydrate Research, 2003

Publication

---

15

Mahesh U. Chhatbar, Ramavatar Meena, Kamalesh Prasad, Dharmesh R. Chejara, A.K. Siddhanta. "Microwave-induced facile synthesis of water-soluble fluorogenic alginic acid derivatives", Carbohydrate Research, 2011

Publication

---

16

Ning Yan, Xiao-Fang Wan, Xin-Sheng Chai. "Simultaneous Determination of the Degree of Deacetylation and Substitution on Carboxymethyl Chitosan by Headspace Gas Chromatography", Journal of Agricultural and Food Chemistry, 2019

Publication

---

17

Melina Pérez-Altamar, Oscar Perales-Pérez. "Fabrication and Characterization of Chitosan/Cellulose-ZnO Nanocomposites for Bactericidal Applications", MRS Proceedings, 2014

Publication

---

18

[docserv.uni-duesseldorf.de](http://docserv.uni-duesseldorf.de)

Internet Source

---

19

Submitted to Universiti Sains Malaysia

Student Paper

---

<1%

<1%

<1%

<1%

<1%

20 Maiti, Sabyasachi, Paramita Dey, Arunava Banik, Biswanath Sa, Somasree Ray, and Santanu Kaity. "Tailoring of locust bean gum and development of hydrogel beads for controlled oral delivery of glipizide", *Drug Delivery*, 2010. <1%

---

21 [helda.helsinki.fi](http://helda.helsinki.fi) <1%  
Internet Source

---

22 Ishaq O. Adisa, Venkata L. Reddy Pullagurala, Jose R. Peralta-Videa, Christian O. Dimkpa et al. "Recent advances in nano-enabled fertilizers and pesticides: a critical review of mechanisms of action", *Environmental Science: Nano*, 2019 <1%

---

23 Maria Jose Retamal, Tomas P. Corrales, Marcelo A. Cisternas, Nicolas H. Moraga et al. "Surface Morphology of Vapor-Deposited Chitosan: Evidence of Solid-State Dewetting during the Formation of Biopolymer Films", *Biomacromolecules*, 2016 <1%

---

24 Xi Chen, Xiaojun Liu, Congcong Miao, Pengfei Song, Yubing Xiong. "Ionic liquid-like inimer mediated RAFT polymerization of N-isopropylacrylamide", *European Polymer Journal*, 2018 <1%

25

M Kurniasih, Purwati, R S Dewi. "Toxicity tests, antioxidant activity, and antimicrobial activity of chitosan", IOP Conference Series: Materials Science and Engineering, 2018

Publication

---

<1%

26

Yang, Shu-Jyuan, Feng-Huei Lin, Kun-Che Tsai, Ming-Feng Wei, Han-Min Tsai, Jau-Min Wong, and Ming-Jium Shieh. "Folic Acid-Conjugated Chitosan Nanoparticles Enhanced Protoporphyrin IX Accumulation in Colorectal Cancer Cells", Bioconjugate Chemistry, 2010.

Publication

---

<1%

27

Yaqin Hu, Tiantian Wu, Chunhua Wu, Shalu Fu, Chunhong Yuan, Shiguo Chen. "Formation and optimization of chitosan-nisin microcapsules and its characterization for antibacterial activity", Food Control, 2017

Publication

---

<1%

28

Thi Phuong Thao Tran, Jean-Charles Bénézet, Anne Bergeret. "Rice and Einkorn wheat husks reinforced poly(lactic acid) (PLA) biocomposites: Effects of alkaline and silane surface treatments of husks", Industrial Crops and Products, 2014

Publication

---

<1%

29

N. M. Bexiga, A. C. Bloise, A. M. Alencar, M. A. Stephano. "Freeze-drying of ovalbumin-loaded

<1%



carboxymethyl chitosan nanocapsules: Impact of freezing and annealing procedures on physicochemical properties of the formulation during dried storage", *Drying Technology*, 2017

Publication

30

[www.tandfonline.com](http://www.tandfonline.com)

Internet Source

<1%

31

Anurag Dobhal, Prachi Bangde, Anomitra Dey, Prajakta Dandekar, Ratnesh Jain. "Chapter 6 Chitosan-Based Nanoparticulate Systems: Implication Towards Therapeutics Application", Springer Science and Business Media LLC, 2017

Publication

<1%

32

[eprints.nottingham.ac.uk](http://eprints.nottingham.ac.uk)

Internet Source

<1%

33

*Studies in Mechanobiology Tissue Engineering and Biomaterials*, 2011.

Publication

<1%

34

[repositorio.unicamp.br](http://repositorio.unicamp.br)

Internet Source

<1%

35

Submitted to University Tun Hussein Onn Malaysia

Student Paper

<1%

36

Wilson, B.. "Poly(n-butylcyanoacrylate) nanoparticles coated with polysorbate 80 for the

<1%

targeted delivery of rivastigmine into the brain to treat Alzheimer's disease", Brain Research, 20080320

Publication

---

37

K. Vivek, L. Harivardhan Reddy, R.S.R. Murthy. "Comparative Study of Some Biodegradable Polymers on the Entrapment Efficiency and Release Behavior of Etoposide from Microspheres", Pharmaceutical Development and Technology, 2008

Publication

---

38

Peng, X.. "Release behavior of microspheres from cross-linked N-methylated chitosan encapsulated ofloxacin", Carbohydrate Polymers, 20060815

Publication

---

39

C. S. Raina, S. Singh, A. S. Bawa, D. C. Saxena. "Some characteristics of acetylated, cross-linked and dual modified Indian rice starches", European Food Research and Technology, 2006

Publication

---

40

[dx.doi.org](https://dx.doi.org/)  
Internet Source

---

41

Prabaharan, M.. "Novel thiolated carboxymethyl chitosan-g-@b-cyclodextrin as mucoadhesive hydrophobic drug delivery carriers",

<1%

<1%

<1%

<1%

<1%

42 Shun-Chieh Hsu, Shan-hui Hsu, Shu-Wei Chang. "Effect of pH on Molecular Structures and Network of Glycol Chitosan", ACS Biomaterials Science & Engineering, 2019 <1%  
Publication

---

43 Submitted to A'Sharqiyah University, Oman <1%  
Student Paper

---

44 Raza, Kaisar, Dinesh Kumar, Chanchal Kiran, Manish Kumar, Santosh Kumar Guru, Pramod Kumar, Shweta Arora, Gajanand Sharma, SHASHI BHUSHAN, and O. P. Katare. "Conjugation of docetaxel with multiwalled carbon nanotubes and co-delivery with piperine: Implications on pharmacokinetic profile and anti-cancer activity.", Molecular Pharmaceutics, 2016. <1%  
Publication

---

45 Submitted to University of Sheffield <1%  
Student Paper

---

46 "Cellulose-Based Superabsorbent Hydrogels", Springer Science and Business Media LLC, 2019 <1%  
Publication

---

47 "Nano-Biomaterials For Ophthalmic Drug Delivery", Springer Nature, 2016 <1%

48

Submitted to University of Bahrain

Student Paper

<1%

---

49

Anjali Singhal, Prashant Kumar Jaiswal, Pawan Kumar Jha, Alka Thapliyal, Indu Shekhar Thakur. " ASSESSMENT OF FOR BIOPULPING OF EUCALYPTUS ", Preparative Biochemistry and Biotechnology, 2013

Publication

<1%

---

50

Tina Chakrabarty, Vinod K. Shahi. "Modified chitosan-based, pH-responsive membrane for protein separation", RSC Adv., 2014

Publication

<1%

---

51

Polysaccharides, 2015.

Publication

<1%

---

Exclude quotes

Off

Exclude matches

Off

Exclude bibliography

Off